Standard Specification for Hubless Cast Iron Soil Pipe and Fittings for Sanitary and Storm Drain, Waste, and Vent Piping Applications¹

This standard is issued under the fixed designation A888; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ε) indicates an editorial change since the last revision or reapproval.

Quarter Bend

Quarter Bend, Reducing

Closet Flange Riser

1. Scope

1.1 This specification covers hubless cast iron soil pipe and fittings for use in gravity flow applications. It establishes standards covering material, manufacture, mechanical and chemical properties, dimensions, coating, test methods, inspection, certification, and product marking for hubless cast iron soil pipe and fittings. These pipe and fittings are intended for non-pressure applications, as the selection of the proper size for sanitary drain, waste, vent, and storm drain systems allows free air space for gravity drainage.

1.2 The EDP/ASA numbers indicated in this section represent a Uniform Industry Code adopted by the American Supply Association (ASA). A group designation prefix, 022, is assigned to hubless products, followed by the four-digit identification assigned to individual items and a check digit. This system has been instituted to facilitate EDP control through distribution channels, and is to be used universally in ordering and specifying product items. Those items with no EDP numbers are either new, special, or transitory and will be assigned numbers on subsequent prints of this specification.

1.3 This specification covers pipe and fittings of the following patterns and applies to any other patterns that conform with the applicable requirements given in this specification.²

1.3.1 Lengths:

EDP/ASA Identification Numbers Fig. 1
for Hubless Pipe
10 ft (3.0 m) in sizes and 5 ft. (1.5 m)
1½, 2, 3, 4, 5, 6, 8,
10, 12, and 15 in.
Method of Specifying Fittings
Fig. 3

1.3.2 Fittings:

Quarter bend, with Side Opening	1 lg. 7
Quarter Bend, With Heel Opening	Fig. 8
Quarter Bend, Tapped	Fig. 9
Quarter Bend, Double	Fig. 10
Quarter Bend, Long	Fig. 11
Short Sweep	Fig. 12
Long Sweep	Fig. 13
Long Sweep, Reducing	Fig. 14
Fifth Bend	Fig. 15
Sixth Bend	Fig. 16
Eighth Bend	Fig. 17
Eighth Bend Long	Fig. 18
Sixteenth Bend	Fig. 19
Sanitary Tee	Fig. 20
Sanitary Tee With Side Opening	Fig. 21
Sanitary Tee With 2 in. Side Opening R or L/R and L	Fig. 22
Sanitary Tee, New Orleans Special With Side Opening	Fig. 23
Sanitary Tee With 45° Side Openings and New Orleans	Fig. 24
Sanitary Special Tee Tapped	Fig. 25
Sanitary Tapped Tee, Horizontal Twin	Fig. 26
Sanitary Tapped Tee, Double Vertical Y Branch	Fig. 27
Y Branch, Double	Fig. 28 Fig. 29
Y Branch, Upright	•
Upright Y Wide Center Florida Special	Fig. 30 Fig. 31
Y Branch, Combination 1/8 Bend	Fig. 32
Y Branch, Combination 1/8 Bend Double	Fig. 33
Sanitary Cross	Fig. 34
Sanitary Cross With Side Opening	Fig. 35
Sanitary Cross, New Orleans, With Side Openings	Fig. 36
Sanitary Cross, New Orleans, With 45° Special and	Fig. 37
Regular Side Openings	1 ig. 07
Sanitary Cross, Tapped	Fig. 38
Test Tee	Fig. 39
Tapped, Extension Piece	Fig. 40
Increaser-Reducer	Fig. 41
Increaser-Reducer, Short	Fig. 42
Tapped Adapter	Fig. 43
Blind Plug	Fig. 44
Iron Body Cleanout-Tapped	Fig. 45
P Trap	Fig. 46
P Trap, Long	Fig. 47
P Trap, Deep Seal	Fig. 48
P Trap, With Primer	Fig. 49
P Trap, With Tapped Inlet	Fig. 50
Tapped Inlet, Double	Fig. 51
Modified Combination Wye and 1/8 Bend, Double	Fig. 52
Modified Combination Wye and 1/8 Bend, Double,	Fig. 53
Extended	9
Two-Way Cleanout	Fig. 54
Twin Cleanout	Fig. 55
Closet Bend, Regular and Reducing	Fig. 56

Fig. 5

Fig. 6

¹ This specification is under the jurisdiction of ASTM Committee A04 on Iron Castings and is under the direct responsibility of Subcommittee A04.12 on Pipes and Tubes.

Current edition approved June 1, 2013. Published June 2013. Originally approved in 1990. Last previous edition approved in 2013 as A888 – 13. DOI: 10.1520/A0888-13A.

² Reprinted with permission from Cast Iron Soil Pipe Institute (CISPI), 1064 Delaware Ave SE, Atlanta, GA 30316, http://www.cispi.org. Available from American National Standards Institute (ANSI), 25 W. 43rd St., 4th Floor, New York, NY 10036, http://www.ansi.org.



Tapping Bosses	Fig. 58
Double Sweep Sanitary Tee (Extended)	Fig. 59
Running Trap with Double Vents	Fig. 60
P Trap with Tapped or Hubless Side Inlet	Fig. 61
Vented Tub Wye Extended, Double	Fig. 62
Vented Tub Wye Extended Offset, Left or Right	Fig. 63
Vented Tub Wye	Fig. 64
Double Two Way Cleanout	Fig. 65

- 1.4 The values stated in inch-pound units are to be regarded as standard. The values given in parentheses are mathematical conversions to SI units that are provided for information only and are not considered standard.
- 1.5 The committee with jurisdiction over this standard is aware of another comparable standard published by the Cast Iron Soil Pipe Institute, CISPI 301.

Note 1—The text of this standard references notes and footnotes that provide explanatory material. These notes and footnotes (excluding those in tables and figures) shall not be considered as requirements of the standard.

2. Referenced Documents

2.1 ASTM Standards:³

A48/A48M Specification for Gray Iron Castings

A644 Terminology Relating to Iron Castings

D1248 Specification for Polyethylene Plastics Extrusion Materials for Wire and Cable

D3960 Practice for Determining Volatile Organic Compound (VOC) Content of Paints and Related Coatings

E8 Test Methods for Tension Testing of Metallic Materials

E1645 Practice for Preparation of Dried Paint Samples by Hotplate or Microwave Digestion for Subsequent Lead Analysis

E2349 Practice for Safety Requirements in Metal Casting Operations: Sand Preparation, Molding, and Core Making; Melting and Pouring; and Cleaning and Finishing

2.2 Federal Standard:⁴

Fed. Std. No. 123 Marking for Shipment (Civil Agencies)

2.3 Military Standard:⁴

MIL-STD-129 Military Marking for Shipment and Storage

2.4 ANSI/ASME Standard:⁵

B1.20 Pipe Threads

2.5 Other Documents:

Uniform Freight Classification Rules⁶

National Motor Freight Classification Rules

Cast Iron Soil Pipe Institute (CISPI) Specification 301 8

3. Terminology

- 3.1 Abbreviations:
- 3.1.1 AC—above center
- 3.1.2 ADAPTR—adapter
- 3.1.3 &—and
- 3.1.4 ASA—American Supply Association
- 3.1.5 ASSY—assembly
- 3.1.6 BD—bend
- 3.1.7 CARL—Carlson
- 3.1.8 *CF*—Carlson fitting
- 3.1.9 *CLO*—closet
- 3.1.10 *CO*—cleanout
- 3.1.11 COMB—combination
- 3.1.12 *CRS*—cross
- 3.1.13 *DB*—double
- 3.1.14 DBL—double
- 3.1.15 *EDP*—electronic data processing
- 3.1.16 EXT—extended, extension
- 3.1.17 *F*—figure
- 3.1.18 FER—ferrule
- 3.1.19 FLNG—flange
- 3.1.20 FTG—fitting
- 3.1.21 HI—high
- 3.1.22 HOR—horizontal
- 3.1.23 *INC*—increaser, increasing
- 3.1.24 *L*—left hand
- 3.1.25 *L*/—less
- 3.1.26 *LG*—long
- 3.1.27 *LH*—left hand
- 3.1.28 *LNG*—long
- 3.1.29 /MAIN—on main
- 3.1.30 MN—on main
- 3.1.31 NO-New Orleans
- 3.1.32 *R*—right hand
- 3.1.33 RAD—radius
- 3.1.34 RED—reducer, reducing
- 3.1.35 REV—revent
- 3.1.36 RH—right hand
- 3.1.37 SAN—sanitary
- 3.1.38 *SD*—side
- 3.1.39 SL & NOTCH-slotted and notched
- 3.1.40 SO—side openings
- 3.1.41 ST—sanitary tap
- 3.1.42 *T*—tee
- 3.1.43 TAP—tap, tapped
- 3.1.44 *TOT*—tap on top
- 3.1.45 *TP*—tap, tapped

³ For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

⁴ Available from Standardization Documents Order Desk, DODSSP, Bldg. 4, Section D, 700 Robbins Ave., Philadelphia, PA 19111-5098, http://www.dodssp.daps.dla.mil.

⁵ Available from American National Standards Institute (ANSI), 25 W. 43rd St., 4th Floor, New York, NY 10036, http://www.ansi.org.

⁶ Available from the Uniform Classification Commission, Room 1106, 222 S. Riverside Plaza, Chicago, IL 60606.

⁷ Available from National Motor Freight Traffic Association (NMFTA), 1001 N. Fairfax St., Alexandria, VA 22314, http://www.nmfta.org.

⁸ Available from Cast Iron Soil Pipe Institute (CISPI), 1064 Delaware Ave SE, Atlanta, GA 30316, http://www.cispi.org.

- 3.1.46 V—vent
- 3.1.47 VERT—vertical
- 3.1.48 W/—with
- 3.1.49 *Y*—wye
- 3.2 Definitions of Terms Specific to This Standard:
- 3.2.1 *manufacturer*—the entity that casts the pipe and fittings covered by this standard.

4. Materials and Manufacture

- 4.1 The pipe and fittings shall be iron castings suitable for installation and service for sanitary, storm drain, waste, and vent piping applications. The pipe and fittings shall meet all applicable requirements and tests given in this specification.
- 4.2 The castings shall be made of cast iron, produced by an established commercial method that provides control over chemical and mechanical properties. Cast iron is a generic term for a series of alloys as defined in Terminology A644 and includes gray iron as well as ductile iron. The castings shall be sound, true to pattern, and of compact close grain that permits drilling and cutting by ordinary methods. The interior surface shall be reasonably smooth and free from defects that would make the castings unfit for the use for which they are intended.
- 4.3 To minimize the possibility of introducing radioactive material to a melting operation, ferrous scrap, pig iron, and any recycled ferrous material shall be screened, by the manufacturer, for radioactivity with detection devices operated in accordance with the detection manufacturer's instructions. Written operating, calibration, and maintenance procedures for the detection equipment shall be provided to the purchaser for review when requested. Records shall be maintained by load of these tests for a period of seven years.
- 4.3.1 Only radiation devices designed specifically for the purpose of screening ferrous material shipments shall be used for the purpose of conforming to this requirement. Hand held radiation detectors (Geiger counters) are not appropriate and shall not be used for the purpose of conforming to this requirement.
- 4.3.2 Material that is found contaminated with radioactivity shall not be used to produce products covered by this specification.
- 4.3.3 Analysis of castings after the time of production shall not be used to determine compliance to this specification.
- 4.4 Foundries manufacturing products to this specification shall comply with all local, provincial, state, and national safety laws and regulations, and with the requirements of Practice E2349.
- 4.5 Pipe and fittings shall not be patched, filled, or welded by the manufacturer to repair cosmetic or material defects that occur during the course of manufacturing.

5. Mechanical Properties

5.1 Mechanical Tests for Gray Iron—The manufacturer shall perform tests to determine mechanical properties of the gray iron used in the manufacture of gray iron soil pipe and

- fittings. Tension test specimens shall be employed. The manufacturer shall maintain a record of mechanical tests for a minimum of 7 years.
- 5.1.1 *Tensile Strength Test*—The tensile strength shall be not less than 21 000 psi (145 MPa).
- 5.1.2 Tension test reports shall include breaking load of test bars, machined diameter of test bar, and calculated tensile strength.
- 5.1.3 Analysis of castings or test bars after the time of production shall not be used as evidence of compliance to this specification.

6. Chemical Test for Gray Iron

6.1 The manufacturer shall perform tests to determine the significant chemical constituents of the gray iron used in the manufacture of gray iron soil pipe and fittings. Analysis shall be performed at the minimum of once per lot as defined in this specification. The manufacturer shall maintain a record of chemical tests performed for a minimum of seven years. The test results shall conform to the following requirements as to chemical composition:

 Phosphorous (P)
 0.38 % Maximum

 Sulfur (S)
 0.15 % Maximum

 Chromium (Cr)
 0.50 % Maximum

 Titanium (Ti)
 0.10 % Maximum

 Aluminum (Al)
 0.50 % Maximum

 Lead (Pb)
 0.015 % Maximum

 Carbon Equivalent
 4.10 % Minimum by mass

 Note: Carbon equivalent for gray iron = %C+%Si/3+%P/3

- 6.1.1 Chemical tests shall be performed at the time of production of the castings covered by this specification.
- 6.1.2 Analysis of castings after the time of production shall not be used as evidence of compliance to this specification.

7. Dimensions and Permissible Variations

- 7.1 *Pipe:*
- 7.1.1 *Ends of Pipe*—The end of pipe shall be cast with or without a spigot bead. The pipe shall be cast in one piece.
- 7.1.2 *Dimensions of Pipe*—Pipe shall be 10 ft (3 m) long or 5 ft (1.5 m) long with the dimensions and tolerances specified in Figs. 1 and 2. (The laying length of pipe is the same as actual length.)
- 7.1.3 Straightness of Pipe—Pipe shall be straight to the extent that for 10-ft (3-m) lengths, deflections in the barrel shall not exceed 5/8 in. (16 mm). For 5-ft (1.5-m) lengths, deflections in the barrel shall not exceed 5/16 in. (8 mm).
 - 7.2 Fittings:
- 7.2.1 Dimensions of Fittings—All fittings shall conform to the dimensions and tolerances specified in Figs. 1 and 2 as applicable. Fittings of the patterns specified in this specification shall conform to the applicable dimensions in Figs. 6–65, inclusive. Fittings not listed shall conform to Fig. 1 for wall thickness and dimension *R* for the minimum radius of any drain inlets that any such fittings provide.
- 7.2.2 All Bends, Sanitary Tees, Stack fittings and special fittings that perform the function of a sanitary tee, designed for the conveyance of soil, waste, or both, affluent, shall have a radius not less than the following:

Nominal Size of Run or Branch (in.)	Minimum Radius
1½ -2	125 % of the smaller run or branch
3 -4	100 % of the smaller run or branch
5 -6	80 % of the smaller run or branch
8 - 10	70 % of the smaller run or branch
12 – 15	60 % of the smaller run or branch

7.2.3 Ends of Fittings—Ends shall have spigot beads as shown in Figs. 1 and 2. Positioning lugs shall be cast on fittings. Positioning lugs shall be as described in Fig. 2 or continuous around circumference of the fitting. Exception: where permitted in Figs. 3–65, spigot beads and gasket positioning lugs shall be optional depending on casting method used. It is permissible to increase the wall thickness on the inside surface of fitting ends. The increased thickness shall not reduce the minimum B dimension in Table 1 in excess of 0.06 in. and shall not extend more than $4\frac{1}{4}$ in. from the plain end. The increased thickness shall be tapered and shall offer no obstruction to flow.

7.2.4 *Pipe Threads*—Screw plugs and tapped openings in fittings shall have taper pipe threads in accordance with ANSI/ASME Standard B1.20.

7.2.5 Internal threads shall be chamfered at the entering end approximately to the major diameter of the thread, at an angle of approximately 45° with the axis of the thread for easy entrance in making a joint and for protection of the thread. The chamfer shall be concentric with the thread and shall be included in the measurement of the thread length.

8. Methods of Specifying Fittings

8.1 *Method of Specifying Sizes of Fittings of More than One Size*—The sizes shall be designated by the order of listing, as follows:

8.1.1 Branch and Tapped Fittings:

8.1.1.1 *Size of Run*—The run shall be that portion of the fitting that forms part of the main pipe line.

8.1.1.2 Size of Branch:

8.2 Methods of Specifying Hand of Fittings with Side Inlets—When placed in the position described below, if the side inlet appears on the right, it shall be a right-hand fitting; if on the left, it shall be a left-hand fitting.

TABLE 1 EDP Identification Numbers for Hubless Pipe

Note 1—When ordering by these EDP numbers, be sure to include the check ($\sqrt{}$) digit following the item number (022 0126 7). This check digit is verification of the group and item number you select.

_	-	-		
Manufacturer's		Code	 Description^A 	
Item	Group	Item No.	\checkmark	- Description
				10 ft (3 m) length
Hubless pipe (see Fig. 1.)		0156	4	11/2
		0158	0	21/2
		0160	6	3
	022	0162	2	4
		0164	8	5
		0168	9	6
		0170	5	8
		0171	3	10
		0172	7	12
		0173	1	15

^A EDP numbers for fittings will appear in each of the respective tables.

- 8.2.1 *Branch Fittings*—The branch shall be placed toward the observer and the outlet end of the run lower than the branch.
- 8.3 The fitting illustrated in Fig. 3 has a right-hand inlet. Left-hand fittings have these openings on the side opposite to that shown. Inlets on fittings shall be made with or without spigot bead and positioning lug.

9. Coating

- 9.1 The pipe and fittings shall be uniformly coated with a material suitable for the purpose that is adherent, not brittle, and without a tendency to scale. The coating shall not contain asbestos above current MSDS reportable levels. Material safety data sheets shall be furnished by the coating manufacturer when requested. The coating shall be evenly and smoothly applied to all surfaces, except in threaded openings.
- 9.2 Pipe and fittings shall not be coated with paint containing lead which exceeds levels above 0.06 % (600 ppm).
- 9.3 The manufacturer shall annually prepare and submit samples to a qualified laboratory for test in accordance with Practice E1645.
- 9.4 Pipe and fittings shall not be coated with paint containing levels of volatile organic hazardous air pollutants (VOHAPs), which exceed levels of 2.6 lb (0.31 kg/L) of VOHAPs per gallon of solids. Reference Practice D3960.
- 9.5 The manufacturer shall prepare and submit samples when changing sources of supply or the coating manufacturer changes formulations for the coating.
 - 9.6 Records shall be maintained for a period of seven years.
- 9.7 Copies of the coating test shall be furnished when requested.

10. Sampling

10.1 Chemical and mechanical tests shall be made regularly and at sufficiently close intervals for adequate determinations of the significant chemical constituents and properties of the cast iron. A specimen taken from a finished product often does not produce the same results as a specimen formed by the method used for sample preparation and is not acceptable for the purposes of testing to this standard. Records of chemical analysis shall be maintained by the manufacturer. Copies of these analyses shall be furnished to the purchaser when requested.

- 10.2 A lot shall consist of one of the following:
- 10.2.1 All the metal poured from a single heating is a batch type furnace.
- 10.2.2 All the metal from two or more batch type melting furnaces poured into a single ladle or a single casting.
- 10.2.3 All the metal poured from a continuous melting furnace for a given period of time between changes in charge, processing conditions, or aim-for chemistry or 4 hours, whichever is the shorter period.

11. Test Methods

11.1 Gray Iron:

- 11.1.1 *Tensile Strength Test*—Test bars shall be cast in accordance with the requirements of Specification A48/A48M. The machined test bar dimensions and drawing and dimensions of as cast test bars are found in Fig. 4. The tensile strength shall be determined in accordance with Test Methods E8.
- 11.1.2 Tension test reports shall include breaking load of test bars, machined diameter of test bar, and calculated tensile strength.

12. Inspection

- 12.1 Inspection and Test by the Manufacturer—Pipe and fittings shall be inspected to verify compliance with this specification. The manufacturer shall maintain a record of all inspections.
- 12.2 Pipe Inspection—At regular intervals (not to exceed 12 h) during the course of production, sample pieces of each size of pipe or pipes being produced shall be selected randomly for inspection. Each pipe selected shall be measured by suitable gages and all dimensions detailed in Fig. 1 of this specification verified to comply with the requirements of this specification. The inspection records shall be maintained by the manufacturer for a period of seven years.
- 12.3 Fitting Inspection—At regular intervals (not to exceed twelve hours) during the course of production, sample pieces of each size and configuration of fitting being produced shall be selected randomly for inspection. Each fitting selected shall be measured by suitable gages to verify that the laying length (as detailed in Figs. 4–65), and all applicable dimensions detailed in Figs. 1 and 2 of this specification comply with the requirements of this specification. The inspection records shall be maintained by the manufacturer for a period of seven years.
- 12.4 *Marking Inspection*—Inspection shall include verification that the markings on pipe and fittings comply with Section 14 of this specification.

13. Certification

13.1 Upon request the purchaser, design professional, or the administrative authority having jurisdiction where the products are being installed shall be furnished certification, by the manufacturer, stating samples representing each lot have been tested and inspected as indicated in this specification and the requirements have been met. If required by the purchaser, design professional, or the administrative authority having jurisdiction where the products are being installed, certification

shall be accompanied by test reports as prepared in accordance with Sections 11 and 12 of this specification. Tension test reports shall include breaking load machined diameters of test bars and calculated tensile strength. Certification shall include legal name and address of the manufacturer.

13.2 Third Party certifiers or inspectors shall utilize the procedures detailed in Annex A1 when conducting inspections at the manufacturing locations.

14. Product Marking


- 14.1 Each length of pipe and each fitting shall be plainly marked with the country of origin and the manufacturer's name or manufacturer's registered trademark by which the manufacturer can be readily identified after installation. The marking shall be adequate identification of the manufacturer of the pipe and fittings if it readily identifies the manufacturer to the end user of the product. Other markings on pipes and fittings shall be permitted provided such markings are not misleading with respect to the identification of the manufacturer by the end user
- 14.1.1 *Pipe Markings*—The pipe shall be marked continuously on the barrel with a minimum of 0.75-in. (19-mm) lettering starting within 3 in. of each end of the pipe. Each pipe shall be marked with the date of manufacture. The marking shall be stenciled on the pipe or otherwise applied so as to be clear and legible.
- 14.1.2 On fittings, the marking shall be cast with raised letters that are not to be located within the "W" dimension, as shown in Fig. 2. Cast markings shall be raised from the wall of the fitting unless otherwise noted.

15. Packaging and Package Marking

15.1 Government Procurement—Unless otherwise specified in the contract, the material shall be packaged in accordance with the supplier's standard practice, which will be acceptable to the carrier at lowest rates. Containers and packing shall comply with Uniform Freight Classification Rules or National Motor Freight Classification Rules. Marking for shipment of such material shall be in accordance with Fed. Std. No. 123 for civil agencies and MIL-STD-129 for military agencies.

16. Keywords

16.1 cast iron; hubless pipe and fittings; no-hub pipe and fittings; soil pipe

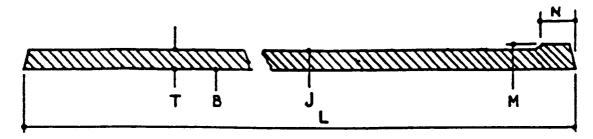


*Pipe shall be with or without a spigot bead.

	Ва	rrel	Sp	igot		Barrel Thickness, T		Louing
Size	Inside Diameter	Outside Diameter	Outside Diameter	Bead Width ^A	Barrel Th			Laying Length, L ^B
OIZO .	В	J	М	N, ±0.13 (3.3)	Nominal	Minimum	W	10 ft ± 0.50 in. (3.0480 m ± 13 mm)
11/2	1.50 ± 0.09	1.90 ± 0.06	1.96 ± 0.06	0.25	0.16	0.13	1.13	120
	(38.1 ± 2.29)	(48.26 ± 1.52)	(49.78±1.52)	(6.35)		(3.3)	(28.7)	(3048)
2	1.96 ± 0.09	2.35± 0.09	2.41 ± 0.09	0.25	0.16	0.13	1.13	120
	(49.8 ± 2.29)	(59.69 ± 2.29)	(61.21 ± 2.29)	(6.35)		(3.3)	(28.7)	(3048)
3	2.96 ± 0.09	3.35 ± 0.09	3.41 ± 0.09	0.25	0.16	0.13	1.13	120
	(75.2 ± 2.29)	(85.09 ± 2.29)	(86.61 ± 2.29)	(6.35)		(3.3)	(28.7)	(3048)
4	3.94 ± 0.09	4.38 + 0.09 - 0.05	4.44 ± 0.09	0.31	0.19	0.15	1.13	120
	(100.08 ± 2.29)	(111.25 + 2.29) (-1.27)	(112.78 ± 2.29)	(7.87)		(3.81)	(28.7)	(3048)
5	4.94 ± 0.09	5.30 + 0.09 - 0.05	5.36 ± 0.09	0.31	0.19	0.15	1.50	120
	(125.48 ± 2.29)	(134.62 + 2.29) (-1.27)	(136.14 ± 2.29)	(7.87)		(3.81)	(38.1)	(3048)
6	5.94 ± 0.09	6.30 + 0.09 - 0.05	6.36 ± 0.09	0.31	0.19	0.15	1.50	120
	(150.88 ± 2.29)	(160.02 + 2.29) (-1.27)	(161.54 ± 2.29)	(7.87)		(3.81)	(38.1)	(3048)
8	7.94 ± 0.13	8.38 + 0.09 - 0.09	8.44 ± 0.09	0.31	0.23	0.17	2.00	120
	(201.68 ± 3.3)	(212.85 + 3.3) (-2.29)	(214.38 ± 2.29)	(7.87)		(4.32)	(50.8)	(3048)
10	10.00 ± 0.13	10.56 ± 0.09	10.62 ± 0.09	0.31	0.28	0.22	2.00	120
	(254 ± 3.3)	(268.22 ± 2.29)	(269.75 ± 2.29)	(7.87)		(5.59)	(50.8)	(3048)
12	11.94 ± 0.13	12.50 ± 0.13	12.62 ± 0.13	0.31	0.28	.22	2.75	120
	(303.28 ± 3.3)	(317.5 ± 3.3)	(320.55 ± 3.3)	(7.87)		(5.59)	(69.85)	(3048)
15	15.11 ± 0.13	15.83 ± 0.13	16.12 ± 0.13	0.31	0.36	.30	2.75	120
	(383.79 ± 3.3)	(402.08 ± 3.3)	(409.45 ± 3.3)	(7.87)		(7.62)	(69.85)	(3048)

FIG. 1 Dimensions and Tolerances in Inches (Millimetres) of Spigots and Barrels for Hubless Pipe and Fittings

A See Fig. 2 for details of the spigot and gasket positioning lug.

B Laying lengths as listed in Fig. 1 shall be for pipe only, and such pipe shall be 10 ft (3 m) long. Laying length for fittings are listed in the applicable tables.

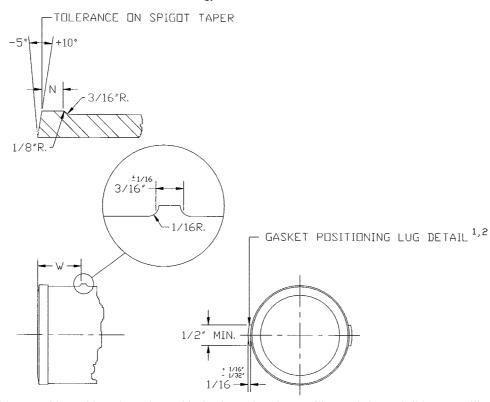

Note 1—Pipe shall be cast with or without the gasket positioning lugs. These lugs, as illustrated above, shall be cast as illustrated or be continuous around the entire circumference.

Note 2—Gasket positioning lugs shall be cast on all fittings except as otherwise noted. These lugs, as illustrated above, shall be cast as illustrated or be continuous around the entire circumference.

Size, in.	Spigot Detail, N in. (mm) ± 0.13 (3.3)	Gasket Lug Location, W in. (mm) ±0.13 (3.3)
11/2	0.25 (6)	1.13 (29)
2	0.25 (6)	1.13 (29)
3	0.25 (6)	1.13 (29)
4	0.31 (8)	1.13 (29)
5	0.31 (8)	1.50 (38)
6	0.31 (8)	1.50 (38)
8	0.31 (8)	2.00 (51)
10	0.31 (8)	2.00 (51)
12	0.31 (8)	2.75 (70)
15	0.31 (8)	2.75 (70)

FIG. 2 Details of Spigot Bead and Gasket Positioning Lug


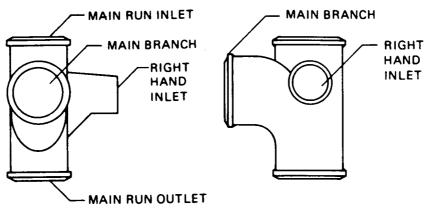


FIG. 3 Specifying Hand of Fittings with Side Inlets or Outlets



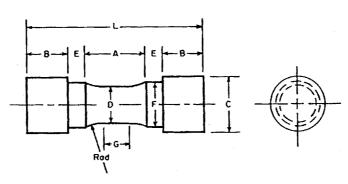

Dimensions, in (mm)

G—Length of parallel, min D—Diameter R—Radius of fillet, min

A-Length of reduced section, min

L-Overall length, min

C—Diameter of end section, approx

E-Length of shoulder, min

F-Diameter of shoulder

B-Length of end section

Tension Test Specimen B

0.75 (19)

 $0.750 \pm 0.015 (19.0 \pm 0.38)$ 1 (25)

11/2 (38) 4 (100)


11/4 (32) 1/4 (6)

 $^{15/_{16}}_{A} \pm ^{1/_{64}} (25 \pm 0.4)$

	As-Cast Diameter, in. (mm)						
Test Bar	Nominal (Mid- Length)	Minimum (Bottom)	Maximum (Top)	Minimum (Specified)	Maximum (Rec- ommended)		
В	1.20 (30.5)	1.14 (29.0)	1.32 (33.5)	6.0 (150)	9.0 (230)		

^A Optional to fit holders on testing machine. If threaded, root diameter shall not be less than dimension F.

FIG. 4 Sample Test Bar

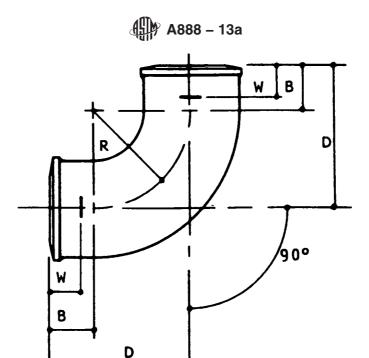


ASA C Group		Size,		Dimensions, in. (mm) ^A			
Item No.	V	– in.	В	D ^B ±1/8 (3.2)	R	W	
0188	7	1½	1½ (38)	41/4 (108)	23/4 (70)	11/8 (29)	
0190	3	2	1½ (38)	41/2 (114)	3 (76)	11/8 (29)	
0192	9	3	1½ (38)	5 (127)	3½ (89)	11/8 (29)	
0194	5	4	1½ (38)	5½ (140)	4 (102)	11/8 (29)	
0196	0	5	2 (51)	6½ (165)	4½ (114)	1½ (38)	
0198	6	6	2 (51)	7 (178)	5 (127)	1½ (38)	
0200	0	8	2½ (64)	8½ (216)	6 (152)	2 (51)	

^A For details of barrel, spigot, and gasket positioning lug, see Figs. 1 and 2. ^B Dimension D is laying length.

FIG. 5 $\frac{1}{4}$ Bend (corresponds to Table 5 of CISPI Specification 301)




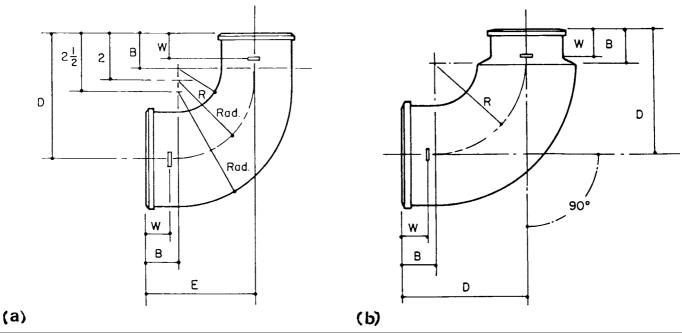

	ASA Code	Group 022				Dimensions, in. (mm	ı) ^A	
			Sizes, in.					
	Item No.	$\sqrt{}$		В	R	$D^B \pm \frac{1}{8} (3.2)$	$E^B \pm \frac{1}{8} (3.2)$	W
Fig. (a)	0218	2	4 by 3	1½ (38)	3½ (89)	5½ (140)	5 (127)	11/8 (29)
Fig. (b)	0218	2	4 by 3	1½ (38)	4 (102)	5½ (140)		11/8 (29)

 $[^]A$ For details of barrel, spigot, and gasket positioning lug, see Figs. 1 and 2. B Dimensions D and E are laying lengths.

FIG. 6 Reducing 1/4 Bend (corresponds to Tables 6 and 7 of CISPI Specification 301)

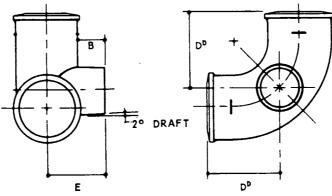

Note 1—For details of 1/4 bend, see Fig. 5.


Note 2-Inclusion of spigot bead and positioning lug optional with manufacturer based on casting method used.

ASA Code C	Group 022	2	Dimensions, in. $(mm)^A$				
		Sizes, in.					
Item No.	\checkmark		В	$E^B \pm \frac{1}{8} (3.2)$	D^B		
0236	4	3 by 2	1½ (38)	31/4 (83)	4 (102)		
0238	0	4 by 2	1½ (38)	3¾ (95)	45/16 (110)		

^A For details of barrel, spigot, and gasket positioning lug, see Figs. 1 and 2.

FIG. 7 1/4 Bend With Side Opening (corresponds to Table 8 of CISPI Specification 301)


^B Dimension E is laying length.

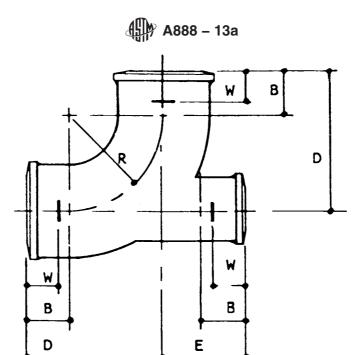

ASA Code Group 022 Dimensions, in. (mm) ^A						4	
		Size, in.					
Item No.	$\sqrt{}$		В	$D^B \pm \frac{1}{8} (3.2)$	$E^B \pm \frac{1}{8} (3.2)$	R	W
0280	2	3 by 2	1½ (38)	5 (127)	27/8 (73)	31/2 (89)	11/8 (29)
0275	2	3 by 2	1½ (38)	5 (127)	101/2 (267)	31/2 (89)	11/8 (29)
0282	8	4 by 2	1½ (38)	5½ (140)	31/4 (83)	4 (102)	11/8 (29)

^A For details of barrel, spigot, and gasket positioning lug, see Figs. 1 and 2. ^B Dimensions D and E are laying lengths.


FIG. 8 1/4 Bend With Heel Opening (corresponds to Table 9 of CISPI Specification 301)

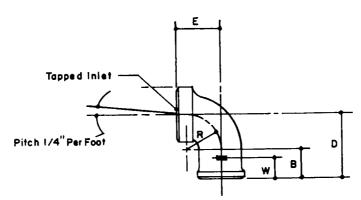

ASA Code Gro	up 022		Dimensions, in. (mm) ^A						
		Size, in.			_		_		
Item No.	$\sqrt{}$		В	E	$D^B \pm \frac{1}{8} (3.2)$	R	IPS Tapping ^C	W	
0324	8	1½ by 1¼	1½ (38)	2 (51)	3 (76)	13/4 (44)	11/4 (32)	11/8 (29)	
0326	3	11/2 by 11/2	1½ (38)	2 (51)	3 (76)	13/4 (44)	11/2 (38)	11/8 (29)	
0328	9	2 by 11/4	1½ (38)	21/4 (57)	31/4 (83)	13/4 (44)	11/4 (32)	11/8 (29)	
0330	5	2 by 1½	1½ (38)	21/4 (57)	31/4 (83)	13/4 (44)	11/2 (38)	11/8 (29)	
		2 by 2	1½ (38)	21/4 (57)	31/4 (83)	13/4 (44)	2 (51)	11/8 (29)	

^A For details of barrel, spigot, and gasket positioning lug, see Figs. 1 and 2. ^B Dimension D is laying length. ^C For details of tapping bosses, see Fig. 58.


FIG. 9 Tapped 1/4 Bend (corresponds to Table 11 of CISPI Specification 301)

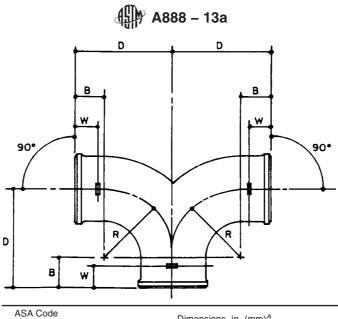

ASA Code Group 022				Dimensio	ns, in. (mm) ^A	
		Size, in				
Item No.			$D^B \pm \frac{1}{8} (3.2)$	R	В	W
0402	2	2	4½ (114)	3 (76)	1½ (38)	11/8 (29)
0404	8	3	5 (127)	3½ (89)	1½ (38)	11/8 (29)
0406	3	4	5½ (140)	4 (102)	1½ (38)	11/8 (29)

^A For details of barrel, spigot, and gasket positioning lug, see Figs. 1 and 2.

FIG. 10 Double $1\!\!/\!_4$ Bend (corresponds to Table 13 of CISPI Specification 301)

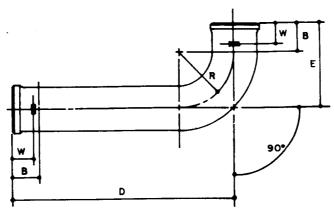


ASA Code Grou	ASA Code Group 022		Dimensions, in. (mm) ^A						
Item No.	$\sqrt{}$	Size, in.	В	E ^B ±1/8 (3.2)	D ^B ±1/8 (3.2)	R	W		
0424	6	2 by 12	1½ (38)	4½ (114)	12 (305)	3 (76)	11/8 (29)		
		2 by 14	1½ (38)	4½ (114)	14 (356)	3 (76)	11/8 (29)		
0423	8	2 by 16	1½ (38)	4½ (114)	16 (406)	3 (76)	11/8 (29)		
0425	3	2 by 18	1½ (38)	4½ (114)	18 (457)	3 (76)	11/8 (29)		
		2 by 24	1½ (38)	4½ (114)	24 (610)	3 (76)	11/8 (29)		
0426	1	3 by 12	1½ (38)	5 (127)	12 (305)	3½ (89)	11/8 (29)		
0427	9	3 by 18	1½ (38)	5 (127)	18 (457)	31/2 (89)	11/8 (29)		
0428	7	4 by 12	1½ (38)	5½ (140)	12 (305)	4 (102)	11/8 (29)		
0431	1	4 by 18	1½ (38)	5½ (140)	18 (457)	4 (102)	11/8 (29)		

^A For details of barrel, spigot, and gasket positioning lug, see Figs. 1 and 2. ^B Dimensions D and E are laying lengths.

FIG. 11 Long 1/4 Bend (corresponds to Table 14 of CISPI Specification 301)

^B Dimension D is laying length.



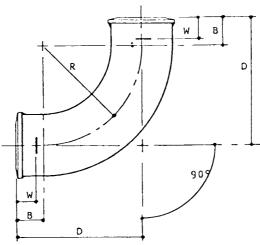


ASA Code Gro	up 022	Cino in	Dimensions, in. (mm) ^A					
Item No.		Size, in.	В	D ^B ±1/8 (3.2)	R	W		
0462	6	2	1½ (38)	6½ (165)	5 (127)	11/8 (29)		
0464	2	3	1½ (38)	7 (178)	5½ (140)	11/8 (29)		
0468	3	4	1½ (38)	7½ (191)	6 (152)	11/8 (29)		
0470	9	5	2 (51)	8½ (216)	6½ (165)	11/2 (38)		
0472	5	6	2 (51)	9 (229)	7 (178)	11/2 (38)		
0474	1	8	21/2 (64)	10½ (267)	8 (203)	2 (51)		
0475	8	10	3 (76)	12 (305)	9 (229)	2 (51)		
0476	8	12	31/4 (83)	131/4 (337)	10 (254)	23/4 (70)		
0477	8	15	31/4 (83)	143/4 (375)	11½ (292)	23/4 (70)		

Extended Pattern											
ASA Code C	Group 022	– Size, in. –	Dimensions, in. (mm) ^A								
Item No.	Item No. √		В	D ^B ±1/8 (3.2)	E ^B ±1/8 (3.2)	R	W				
0478	7	2 by 12	1½ [38]	6½ [165]	12 [305]	5 [127]	11/8 [29]				
0479	7	2 by 14	1½ [38]	6½ [165]	14 [356]	5 [127]	11/8 [29]				
0480	7	2 by 16	1½ [38]	6½ [165]	16 [406]	5 [127]	11/8 [29]				
0481	7	2 by 18	1½ [38]	6½ [165]	18 [457]	5 [127]	11/8 [29]				
0482	7	2 by 24	1½ [38]	6½ [165]	24 [610]	5 [127]	11/8 [29]				
0483	7	2 by 34	1½ [38]	6½ [165]	34 [864]	5 [127]	11/8 [29]				
Note: Dimensions	D and E are lay	ying lengths on exter	nded pattern fittings.			•					

^A For details of barrel, spigot, and gasket positioning lug, see Figs. 1 and 2. ^B Dimension D is laying length.


FIG. 12 Short Sweep (corresponds to Table 15 of CISPI Specification 301)

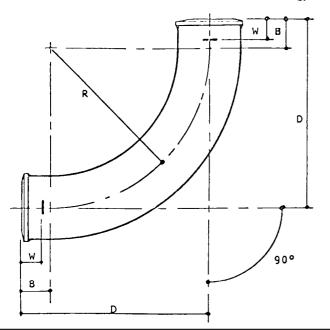

ASA Code Group 022		Size,		Dimensions, in. (mm) ^A						
Item No.	$\sqrt{}$	- 111.	В	$D^B \pm \frac{1}{8}$ (3.3)	2) R	W				
0492	3	11/2	1½ (38)	91/4 (235)	73/4 (197)	11/8 (29)				
0494	9	2	1½ (38)	91/2 (241)	8 (203)	11/8 (29)				
0496	4	3	1½ (38)	10 (254)	81/2 (216)	11/8 (29)				
0498	0	4	1½ (38)	10½ (267)	9 (229)	11/8 (29)				
0500	3	5	2 (51)	11½ (292)	9½ (241)	1½ (38)				
0502	9	6	2 (51)	12 (305)	10 (254)	1½ (38)				

^A For details of barrel, spigot, and gasket positioning lug, see Figs. 1 and 2. ^B Dimension D is laying length.


FIG. 13 Long Sweep (corresponds to Table 17 of CISPI Specification 301)

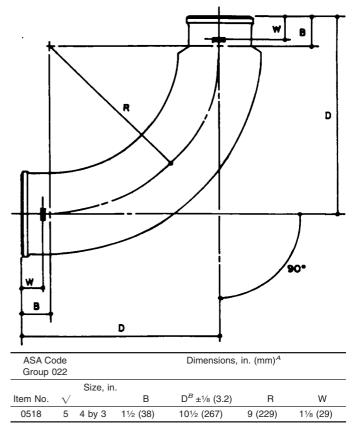

^A For details of barrel, spigot, and gasket positioning lug, see Figs. 1 and 2. ^B Dimension D is laying length.

FIG. 14 Reducing Long Sweep (corresponds to Table 18 of CISPI Specification 301)






ASA Co Group (Dimensions,	in. (mm) ^A	
		Size, in.				
Item No.	\vee		В	$D^B \pm \frac{1}{8} (3.2)$	R	W
0536	7	2	1½ (38)	311/16 (94)	3 (76)	11/8 (29)
0538	3	3	1½ (38)	41/16 (103)	3½ (89)	11/8 (29)
0540	9	4	1½ (38)	47/16 (113)	4 (102)	11/8 (29)

 $^{^{}A}$ For details of barrel, spigot, and gasket positioning lug, see Figs. 1 and 2. B Dimension D is laying length.

FIG. 15 1/5 Bend (corresponds to Table 19 of CISPI Specification 301)




ASA Co Group (Dimensions,	in. (mm) ^A	
		Size, iı	٦.			
Item No.	\checkmark		В	$D^B \pm \frac{1}{8} (3.2)$	R	W
0570	6	2	1½ (38)	31/4 (83)	3 (76)	11/8 (29)
0572	2	3	1½ (38)	3½ (89)	3½ (89)	11/8 (29)
0574	8	4	1½ (38)	313/16 (97)	4 (102)	11/8 (29)

 $^{^{\}it A}$ For details of barrel, spigot, and gasket positioning lug, see Figs. 1 and 2. $^{\it B}$ Dimension D is laying length.

FIG. 16 1/6 Bend (corresponds to Table 20 of CISPI Specification 301)






ASA Code Group 022		Size, in		Dimensions	, in. (mm) ^A	
Item No.	\vee	_	В	$D^B \pm \frac{1}{8} (3.2)$	R	W
0604	3	11/2	1½ (38)	25/8 (67)	23/4 (70)	11/8 (29)
0606	8	2	1½ (38)	23/4 (70)	3 (76)	11/8 (29)
0608	4	3	1½ (38)	3 (76)	3½ (89)	11/8 (29)
0610	0	4	11/2 (38)	31/8 (79)	4 (102)	11/8 (29)
0612	6	5	2 (51)	37/8 (98)	41/2 (114)	1½ (38)
0614	2	6	2 (51)	41/16 (103)	5 (127)	1½ (38)
0616	7	8	21/2 (64)	5 (127)	6 (152)	2 (51)
0617	5	10	3 (76)	5 ¹⁵ / ₁₆ (151)	7 (178)	2 (51)
0618	5	12	3 1/4 (83)	6 % (167)	8 (203)	2 3/4 (70)
0619	5	15	3 1/4 (83)	7 3/16 (183)	9 ½ (241)	2 ¾ (70)

^A For details of barrel, spigot, and gasket positioning lug, see Figs. 1 and 2.

FIG. 17 1/8 Bend (corresponds to Table 21 of CISPI Specification 301)

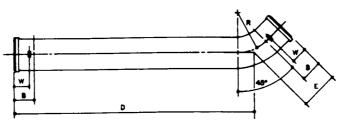


ASA Code Group 022		Cina in	Dimensions, in. (mm) ^A					
Item No.		Size, in.	В	E ^B ±1/8 (3.2)	D ^B ±1/8 (3.2)	R	W	
0638	1	2 by 6	1½ (38)	23/4 (70)	6 (152)	3 (76)	11/8 (29)	
		2 by 12	1½ (38)	23/4 (70)	12 (305)	3 (76)	11/8 (29)	
		2 by 14	1½ (38)	23/4 (70)	14 (356)	3 (76)	11/8 (29)	
0641	5	2 by 16	1½ (38)	23/4 (70)	16 (406)	3 (76)	11/8 (29)	
0643	1	2 by 18	1½ (38)	23/4 (70)	18 (457)	3 (76)	11/8 (29)	
0640	7	3 by 12	1½ (38)	3 (76)	12 (305)	3½ (89)	11/8 (29)	
0644	9	3 by 18	1½ (38)	3 (76)	18 (457)	31/2 (89)	11/8 (29)	
0642	3	4 by 12	1½ (38)	31/8 (79)	12 (305)	4 (102)	11/8 (29)	

^A For details of barrel, spigot, and gasket positioning lug, see Figs. 1 and 2. ^B Dimensions D and E are laying lengths.

FIG. 18 Long 1/8 Bend (corresponds to Table 22 of CISPI Specification 301)

 $^{^{\}it B}$ Dimension D is laying length.






ASA Code 022		Size,	Dimensions, in. $(mm)^A$					
Item No.	V	in.	В	D ^B ±½ (3.2)	R	W		
0676	1	11/2	1½ (38)	21/8 (54)	23/4 (70)	11/8 (29)		
0678	7	2	1½ (38)	21/8 (54)	3 (76)	11/8 (29)		
0680	3	3	1½ (38)	21/4 (57)	31/2 (89)	11/8 (29)		
0682	9	4	1½ (38)	25/16 (59)	4 (102)	11/8 (29)		
0684	5	5	2 (51)	27/8 (73)	41/2 (114)	1½ (38)		
0686	0	6	2 (51)	3 (76)	5 (127)	1½ (38)		
0688	6	8	21/2 (64)	3¾ (95)	6 (152)	2 (51)		

^A For details of barrel, spigot, and gasket positioning lug, see Figs. 1 and 2. ^B Dimension D is laying length.


FIG. 19 $1\!\!/_{16}$ Bend (corresponds to Table 23 of CISPI Specification 301)

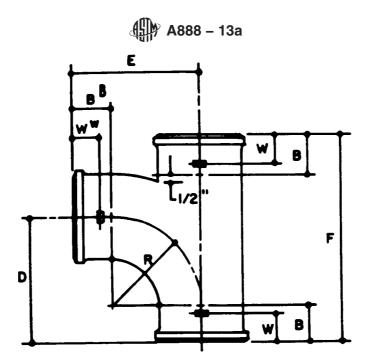

ASA Code Group 022		Size, in.				Dimensio	ons, in. (mm) ^A			
Item No.			В	E ^B ±1/8 (3.2)	F ^B ±1/8 (3.2)	D	R	W	WW	B ^B
0806	4	11/2	1½ (38)	41/4 (108)	6½ (165)	41/4 (108)	23/4 (70)	11/8 (29)	11/8 (29)	1½ (38)
0808	0	2 by 1½	11/2 (38)	41/2 (114)	65/8 (168)	41/4 (108)	23/4 (70)	11/8 (29)	11/8 (29)	1½ (38)
0810	6	2	11/2 (38)	4½ (114)	67/8 (175)	41/2 (114)	3 (76)	11/8 (29)	11/8 (29)	1½ (38)
0812	2	3 by 1½	11/2 (38)	5 (127)	61/2 (165)	41/4 (108)	23/4 (70)	11/8 (29)	11/8 (29)	1½ (38)
0814	8	3 by 2	1½ (38)	5 (127)	67/8 (175)	41/2 (114)	3 (76)	11/8 (29)	11/8 (29)	1½ (38)
0816	3	3	11/2 (38)	5 (127)	8 (203)	5 (127)	3½ (89)	11/8 (29)	11/8 (29)	1½ (38)
0818	9	4 by 2	11/2 (38)	5½ (140)	67/8 (175)	4½ (114)	3 (76)	11/8 (29)	11/8 (29)	1½ (38)
0820	5	4 by 3	11/2 (38)	5½ (140)	8 (203)	5 (127)	3½ (89)	11/8 (29)	11/8 (29)	1½ (38)
0822	1	4	11/2 (38)	5½ (140)	91/8 (232)	5½ (140)	4 (102)	11/8 (29)	11/8 (29)	1½ (38)
0824	7	5 by 2	2 (51)	6½ (165)	81/2 (216)	5 (127)	3 (76)	11/2 (38)	11/8 (29)	1½ (38)
0826	2	5 by 3	2 (51)	6 (152)	95/16 (237)	5½ (140)	3½ (89)	11/2 (38)	11/8 (29)	1½ (38)
0828	8	5 by 4	2 (51)	6 (152)	1013/32 (264)	6 (152)	4 (102)	11/2 (38)	11/8 (29)	1½ (38)
0830	4	5	2 (51)	6½ (165)	117/16 (291)	6½ (165)	41/2 (114)	11/2 (38)	1½ (38)	2 (51)
0832	0	6 by 2	2 (51)	6½ (165)	83/16 (208)	5 (127)	3 (76)	11/2 (38)	11/8 (29)	1½ (38)
0838	0	6 by 3	2 (51)	6½ (165)	93/16 (233)	5½ (140)	3½ (89)	11/2 (38)	11/8 (29)	1½ (38)
0834	6	6 by 4	2 (51)	6½ (165)	101/16 (256)	6 (152)	4 (102)	11/2 (38)	11/8 (29)	1½ (38)
0835	3	6 by 5	2 (51)	7 (178)	11½ (292)	61/2 (165)	41/2 (114)	11/2 (38)	1½ (38)	2 (51)
0836	1	6	2 (51)	7 (178)	12½ (318)	7 (178)	5 (127)	11/2 (38)	11/2 (38)	2 (51)
0848	3	8 by 3	21/2 (64)	7½ (190)	10% (264)	6 (152)	31/2 (89)	2 (51)	11/8 (29)	1½ (38)
0846	4	8 by 4	21/2 (64)	7½ (190)	111/2 (292)	61/2 (165)	4 (102)	2 (51)	11/8 (29)	1½ (38)
0844	5	8 by 5	21/2 (64)	8 (203)	12½ (318)	7 (178)	41/2 (114)	2 (51)	1½ (38)	2 (51)
0842	6	8 by 6	21/2 (64)	8 (203)	131/2 (343)	7½ (191)	5 (127)	2 (51)	1½ (38)	2 (51)
0840	1	8	21/2 (64)	8½ (216)	15½ (395)	81/2 (216)	6 (152)	2 (51)	2 (51)	21/2 (64)

^A For details of barrel, spigot, and gasket positioning lug, see Figs. 1 and 2. ^B Dimensions E and F are laying lengths.

FIG. 20 Sanitary Tee Branch (corresponds to Table 24 of CISPI Specification 301)

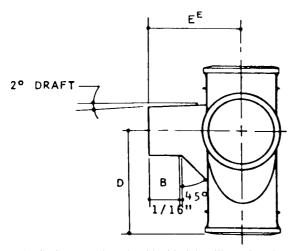


Note 1-Sanitary Tee branch with side inlet; illustration shows left hand. Can be furnished left or right hand.

Note 2-Inclusion of spigot bead and positioning lug optional with manufacturer based on casting method used.

ASA Coo Group 02		Size, in.	Dimensions, in. (mm) ^{A,B}				
Item No.		_	В	E ^{EC} ±1/8 (3.2)	D		
0976	5	3 by 3 by 2 LH	1½ (38)	47/16 (113)	5 (127)		
0986	4	3 by 3 by 2 RH	1½ (38)	47/16 (113)	5 (127)		
0978	1	4 by 2 by 2 LH	1½ (38)	31/4 (83)	4½ (114)		
0988	0	4 by 2 by 2 RH	1½ (38)	31/4 (83)	41/2 (114)		
0980	7	4 by 3 by 2 LH	1½ (38)	415/16 (125)	5 (127)		
0990	6	4 by 3 by 2 RH	1½ (38)	415/16 (125)	5 (127)		
0982	3	4 by 4 by 2 LH	1½ (38)	415/16 (125)	5½ (140)		
0992	2	4 by 4 by 2 RH	1½ (38)	415/16 (125)	5½ (140)		

 $^{^{\}it A}$ For details of barrel, spigot, and gasket positioning lug, see Figs. 1 and 2.

FIG. 21 Sanitary Tee With Right or Left Side Opening (corresponds to Table 28 of CISPI Specification 301)

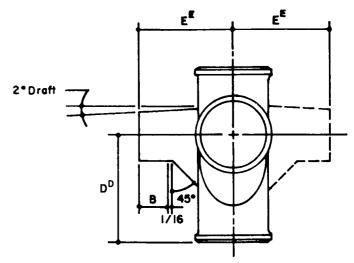

Note 1-Sanitary Tee branch with side inlet; illustration shows left hand. Can be furnished left or right hand.

Note 2—Inclusion of spigot bead and positioning lug optional with manufacturer based on casting method used.

ASA Co Group 0		Size, in.	Dimensions, in. (mm) ^{A,B}					
Item No.	V	_	В	E ^{EC} ±1/8 (3.2)	D			
1030	0	3 by 3 by 2 LH	1½ (38)	47/16 (113)	5 (127)			
1034	2	3 by 3 by 2 RH	1½ (38)	47/16 (113)	5 (127)			
1037	5	3 by 3 by 2 R&L	1½ (38)	47/16 (113)	5 (127)			
1032	6	4 by 4 by 2 LH	1½ (38)	415/16 (125)	5½ (140)			
1036	7	4 by 4 by 2 RH	1½ (38)	415/16 (125)	5½ (140			
1038	3	4 by 4 by 2 R&L	1½ (38)	415/16 (125)	5½ (140)			

 $^{^{\}it A}$ For details of barrel, spigot, and gasket positioning lug, see Figs. 1 and 2.

FIG. 22 Sanitary Tee With 2-in. Side Opening Right or Left/Right and Left (corresponds to Table 29 of CISPI Specification 301)


^B For details of sanitary Tee branch, see Fig. 20.

^C Dimension E^E is laying length.

^B For details of sanitary Tee branch, see Fig. 20.

^C Dimension E^E is laying length.



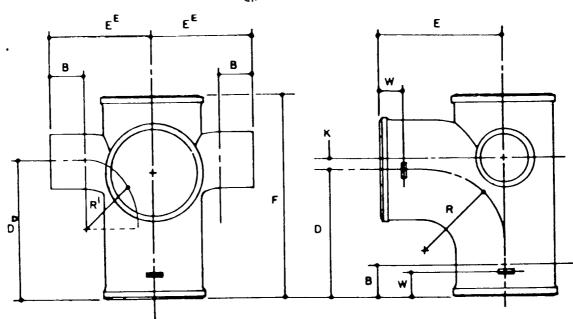


Note 1—Inclusion of spigot bead positioning lug optional with manufacturer based on casting methods used.

ASA Co Group 0		Cina in				Di	mensions, ir	ı. (mm) ^A				
Item No.	V	– Size, in.	В	E ^{EB} ±½ (3.2)	$E^B \pm \frac{1}{8}$ (3.2)	F ^B ±½ (3.2)	D	D^D	K	R^A	R	W
1058	1	3 by 3 by 2 LH	1½ (38)	41/2 (114)	5 (127)	81/2 (216)	5 (127)	6 (152)	1 (25)	3 (76)	3½ (89)	11/8 (29)
1062	3	3 by 3 by 2 RH	1½ (38)	41/2 (114)	5 (127)	81/2 (216)	5 (127)	6 (152)	1 (25)	3 (76)	31/2 (89)	11/8 (29)
1066	4	3 by 3 by 2 R&L	1½ (38)	41/2 (114)	5 (127)	81/2 (216)	5 (127)	6 (152)	1 (25)	3 (76)	31/2 (89)	11/8 (29)
1060	7	4 by 4 by 2 LH	1½ (38)	5 (127)	5½ (140)	91/8 (232)	5½ (140)	6½ (165)	1 (25)	3 (76)	4 (102)	11/8 (29)
1064	9	4 by 4 by 2 RH	1½ (38)	5 (127)	5½ (140)	91/8 (232)	5½ (140)	61/2 (165)	1 (25)	3 (76)	4 (102)	11/8 (29)
1068	0	4 by 4 by 2 R&L	1½ (38)	5 (127)	5½ (140)	91/8 (232)	5½ (140)	6½ (165)	1 (25)	3 (76)	4 (102)	11/8 (29)

^A For details of barrel, spigot, and gasket positioning lug, see Figs. 1 and 2. ^B Dimensions E, F, and E^E are laying lengths.

FIG. 23 Sanitary Tee With Side Opening Above Center Right and Left—Right or Left (New Orleans Special) (corresponds to Table 30 of CISPI Specification 301)



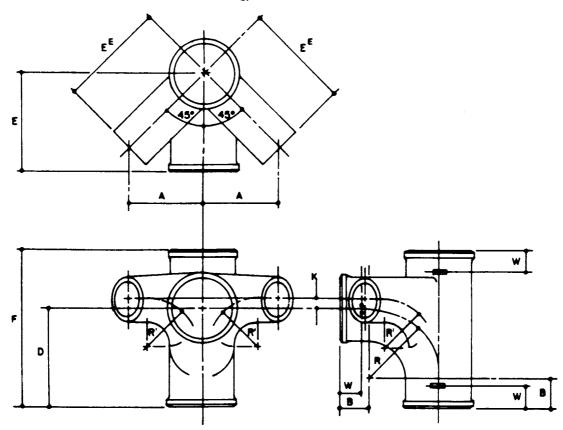


Note 1-Inclusion of spigot bead and positioning lug optional with manufacturer based on casting methods used. Note 2—For details of Sanitary Tee ranch, see Fig. 20.

ASA Co Group 0							Dimension	ns, in. (mm) ^A				
Item No.	V	Size, in.	А	В	E ^{EB} ±½ (3.2)	E ^B ±½ (3.2)	F ^B ±½ (3.2)	D	К	R	R'	W
1086	2	3 by 3 by 2 LH	33/4 (95)	1½ (38)	53/8 (137)	5 (127)	8 (203)	5 (127)	1/2 (13)	3½ (89)	3 (76)	11/8 (29)
1090	4	3 by 3 by 2 RH	33/4 (95)	1½ (38)	5% (137)	5 (127)	8 (203)	5 (127)	1/2 (13)	31/2 (89)	3 (76)	11/8 (29)
1094	6	3 by 3 by 2 by 2 R&L	3¾ (95)	1½ (38)	5% (137)	5 (127)	8 (203)	5 (127)	1/2 (13)	3½ (89)	3 (76)	11/8 (29)
							F ^B N.O. ±½ (3.2)		KNO			
1122	5	3 by 3 by 2 LH	3¾ (95)	1½ (38)	5% (137)	5 (127)	8½ (216)	5 (127)	1 (25)	3½ (89)	3 (76)	11/8 (29)
1126	6	3 by 3 by 2 RH	3¾ (95)	1½ (38)	5% (137)	5 (127)	81/2 (216)	5 (127)	1 (25)	31/2 (89)	3 (76)	11/8 (29)
1130	8	3 by 3 by 2 R&L	3¾ (95)	11/2 (38)	5% (137)	5 (127)	81/2 (216)	5 (127)	1 (25)	31/2 (89)	3 (76)	11/8 (29)
1124	1	4 by 4 by 2 LH	45/16 (110)	1½ (38)	61/8 (156)	5½ (140)	91/8 (232)	5½ (140)	1 (25)	4 (102)	3 (76)	11/8 (29)
1128	2	4 by 4 by 2 RH	45/16 (110)	1½ (38)	61/8 (156)	5½ (140)	91/8 (232)	5½ (140)	1 (25)	4 (102)	3 (76)	11/8 (29)
1132	4	4 by 4 by 2 R&L	45/16 (110)	1½ (38)	61/8 (156)	5½ (140)	91/8 (232)	5½ (140)	1 (25)	4 (102)	3 (76)	11/8 (29)

 $[^]A$ For details of barrel, spigot, and gasket positioning lug, see Figs. 1 and 2. B Dimensions E, F, and E E are laying lengths.

Sanitary Tee With 45° Side Openings Above Center Right or Left or Right and Left^B and New Orleans Specials (corresponds to Table 31 of CISPI Specification 301) FIG. 24

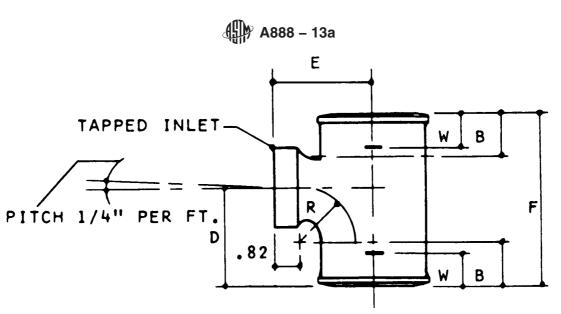


ASA Code Grou	ıp 022	0: :			D	imensions, in. (ı	mm) ^A		
Item No.		- Size, in.	В	E	F ^B ±½ (3.2)	D	R	IPS Tapping $^{\mathcal{C}}$	W
1208	2	1½ by 1¼	1½ (38)	29/16 (65)	511/16 (144)	31/4 (83)	13/4 (44)	11/4 (32)	11/8 (29)
1210	8	11/2 by 11/2	1½ (38)	29/16 (65)	5 ¹¹ / ₁₆ (144)	31/4 (83)	13/4 (44)	11/2 (38)	11/8 (29)
1212	4	2 by 11/4	1½ (38)	213/16 (71)	511/16 (144)	31/4 (83)	13/4 (44)	11/4 (32)	11/8 (29)
1214	0	2 by 1½	1½ (38)	213/16 (71)	511/16 (144)	31/4 (83)	13/4 (44)	11/2 (38)	11/8 (29)
1216	5	2 by 2	11/2 (38)	31/16 (78)	6% (162)	3¾ (95)	21/4 (57)	2 (51)	11/8 (29)
1218	1	3 by 11/4	1½ (38)	35/16 (84)	511/16 (144)	31/4 (83)	13/4 (44)	11/4 (32)	11/8 (29)
1220	7	3 by 1½	1½ (38)	35/16 (84)	5 ¹¹ / ₁₆ (144)	31/4 (83)	13/4 (44)	11/2 (38)	11/8 (29)
1222	3	3 by 2	1½ (38)	3%16 (90)	6% (162)	33/4 (95)	21/4 (57)	2 (51)	11/8 (29)
1223	1	3 by 3	1½ (38)	43/16 (106)	8 (203)	47/8 (124)	31/2 (89)	3 (76)	11/8 (29)
1224	9	4 by 11/4	1½ (38)	313/16 (97)	511/16 (144)	31/4 (83)	13/4 (44)	11/4 (32)	11/8 (29)
1226	4	4 by 1½	1½ (38)	313/16 (97)	511/16 (144)	31/4 (83)	13/4 (44)	11/2 (38)	11/8 (29)
1228	0	4 by 2	1½ (38)	41/16 (103)	6% (162)	3¾ (95)	21/4 (57)	2 (51)	11/8 (29)
		4 by 3							
1232	2	5 by 1½	2 (51)	45/16 (109)	611/16 (170)	3¾ (95)	13/4 (44)	11/2 (38)	11/2 (38)
1233	0	5 by 2	2 (51)	4%16 (109)	715/16 (202)	41/4 (108)	21/4 (57)	2 (51)	11/2 (38)
1234		6 by 1½	2 (51)	51/16 (129)	611/16 (170)	33/4 (95)	13/4 (44)	11/2 (38)	11/2 (38)
1235		6 by 2	2 (51)	51/16 (129)	77/16 (189)	41/16 (103)	21/16 (52)	2 (51)	11/2 (38)

ASA Code Gro	up 022	- Size, in.			D	imensions, in. (m	m) ^A		
Item No.	$\sqrt{}$	Size, III.	В	E	F ^B ±½ (3.2)	D	R	IPS Tapping $^{\mathcal{C}}$	W
1236	0	2 by 1½	1½ (38)	213/16 (71)	227/8 (581)	2015/16 (532)	13/4 (44)	1½ (38)	11/8 (29)
1237	0	2 by 1½	11/2 (38)	213/16 (71)	31 (787)	291/16 (738)	13/4 (44)	11/2 (38)	11/8 (29)
1238	0	2 by 2	11/2 (38)	31/16 (78)	31 (787)	28% (721)	21/4 (57)	2 (51)	11/8 (29)
1239	0	2 by 2	1½ (38)	31/16 (78)	227/8 (581)	28% (721)	21/4 (57)	2 (51)	11/8 (29)

A For details of barrel, spigot, and gasket positioning lug, see Figs. 1 and 2.
 B Dimension F is laying length.
 C For details of tapping bosses, see Fig. 58.

FIG. 25 Sanitary Tapped Tee (corresponds to Table 32 of CISPI Specification 301)



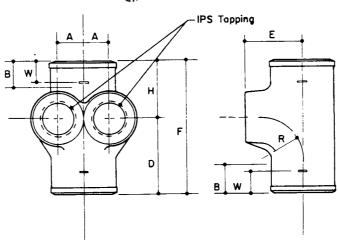


Note 1—Horizontal inlet waste bosses to be tapped at an angle of 1/4 in. (6 mm) per foot to provide flow.

ASA Code 0	roup	Size, in.				Dim	ensions, in.	(mm) ^A			
Item No.		_	В	Н	E	F ^B ±1/8 (3.2)	D	Α	R	W	IPS Tapping $^{\mathcal{C}}$
1290	0	2 by 1½	1½ (38)	3 (76)	21/2 (64)	7 (178)	4 (102)	1% (35)	21/4 (57)	11/8 (29)	11/2 (38)
1292	6	3 by 1½	1½ (38)	3 (76)	3 (76)	7 (178)	4 (102)	1% (35)	21/4 (57)	11/8 (29)	11/2 (38)
1294	2	4 by 1½	1½ (38)	3 (76)	3½ (89)	7 (178)	4 (102)	1% (35)	21/4 (57)	11/8 (29)	1½ (38)

^A For details of barrel, spigot, and gasket positioning lug, see Figs. 1 and 2.

FIG. 26 Horizontal Twin Sanitary Tapped Tee (corresponds to Table 37 of CISPI Specification 301)

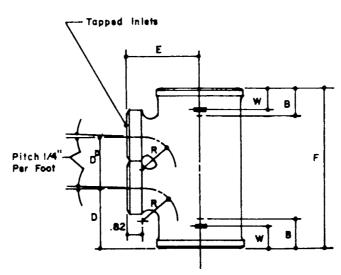

ASA Code G	roup					Dimens	sions, in. (mm) ^A			
022		Size, in.								
Item No.	V	_	В	Е	F ^B ±½ (3.2)	D	D^D	R	IPS Tapping $^{\mathcal{C}}$	W
1304	9	2 by 1½	1½ (38)	213/16 (71)	9¾ (247)	31/4 (83)	41/2 (114)	13/4 (44)	1½ (38)	11/8 (29)

A For details of barrel, spigot, and gasket positioning lug, see Figs. 1 and 2.
B Dimension F is laying length.


Double Vertical Sanitary Tapped Tee (corresponds to Table 38 of CISPI Specification 301)

^B Dimension F is laying length.

^C For details of tapping bosses, see Fig. 58.

^C For details of tapping bosses, see Fig. 58.






ASA Code Gro	up 022	0: :-			D	imensions, in. (m	m) ^A		
Item No.		- Size, in.	В	B ^B	D ^B ±1/8 (3.2)	F ^B ±½ (3.2)	G	W	WW
1312	2	11/2	1½ (38)	1½ (38)	4 (102)	6 (152)	2 (51)	11/8 (29)	11/8 (29)
1314	8	2	1½ (38)	1½ (38)	45/8 (117)	65/8 (168)	2 (51)	11/8 (29)	11/8 (29)
1315	3	3 by 1½	1½ (38)	1½ (38)	45/8 (117)	65/8 (168)		11/8 (29)	11/8 (29)
1316	3	3 by 2	1½ (38)	1½ (38)	55/16 (135)	65/8 (168)	1½ (38)	11/8 (29)	11/8 (29)
1318	9	3	1½ (38)	1½ (38)	53/4 (146)	8 (203)	21/4 (57)	11/8 (29)	11/8 (29)
1320	5	4 by 2	1½ (38)	1½ (38)	6 (152)	65/8 (168)	1 (25)	11/8 (29)	11/8 (29)
1322	1	4 by 3	1½ (38)	1½ (38)	6½ (165)	8 (203)	111/16 (43)	11/8 (29)	11/8 (29)
1324	7	4	1½ (38)	1½ (38)	71/16 (179)	91/2 (241)	27/16 (62)	11/8 (29)	11/8 (29)
1326	2	5 by 2	2 (51)	1½ (38)	7½ (191)	81/16 (205)	15/16 (24)	11/2 (38)	11/8 (29)
1328	8	5 by 3	2 (51)	1½ (38)	8 (203)	911/16 (246)	111/16 (43)	11/2 (38)	11/8 (29)
1330	4	5 by 4	2 (51)	1½ (38)	8½ (216)	113/16 (284)	27/16 (62)	1½ (38)	11/8 (29)
1332	0	5	2 (51)	2 (51)	9½ (241)	125/s (321)	31/8 (79)	11/2 (38)	1½ (38)
1334	6	6 by 2	2 (51)	1½ (38)	81/4 (210)	85/16 (211)	1/2 (13)	11/2 (38)	11/8 (29)
1336	1	6 by 3	2 (51)	1½ (38)	83/4 (222)	93/4 (248)	11/4 (32)	11/2 (38)	11/8 (29)
1338	7	6 by 4	2 (51)	1½ (38)	91/4 (235)	113/16 (284)	115/16 (49)	11/2 (38)	11/8 (29)
1340	3	6 by 5	2 (51)	2 (51)	101/4 (260)	12½ (318)	29/16 (65)	1½ (38)	1½ (38)
1342	9	6	2 (51)	2 (51)	10¾ (273)	141/16 (357)	35/16 (84)	1½ (38)	1½ (38)
1344	5	8 by 2	2½ (64)	21/4 (57)	9% (238)	81/2 (216)	9/16 (14)	2 (25)	11/8 (29)
1346	0	8 by 3	2½ (64)	21/4 (57)	913/16 (249)	915/16 (252)	1/8 (3)	2 (25)	11/8 (29)
1348	6	8 by 4	2½ (64)	21/4 (57)	10% (264)	117/16 (291)	15/16 (24)	2 (25)	11/8 (29)
1350	2	8 by 5	21/2 (64)	23/4 (70)	11% (289)	1213/16 (325)	15/8 (41)	2 (25)	1½ (38)
1352	8	8 by 6	2½ (64)	23/4 (70)	11 ¹³ / ₁₆ (300)	143/16 (360)	25/16 (59)	2 (25)	1½ (38)
1354	4	8	2½ (64)	31/4 (83)	13% (340)	171/8 (435)	33/4 (95)	2 (25)	2 (51)
1357	7	10 by 4	3 (76)	1½ (38)	1111/16 (297)	125/8 (321)	3/4 (19)	2 (25)	11/8 (29)
1359	3	10 by 6	3 (76)	2 (51)	131/8 (333)	157/16 (392)	23/16 (56)	2 (25)	1½ (38)
1360	0	10 by 8	3 (76)	2½ (64)	1411/16 (373)	18% (467)	35/8 (92)	2 (25)	2 (51)
1361	9	10	3 (76)	33/4 (95)	16½ (419)	21½ (546)	51/16 (129)	2 (25)	2 (51)
1362	9	12	31/4 (83)	31/4 (83)	19¾ (502)	25½ (648)	53/4 (146)	23/4 (70)	23/4 (70)
1363	9	15	31/4 (83)	31/4 (83)	231/4 (591)	30 (762)	63/4 (171)	23/4 (70)	23/4 (70)

^A For details of barrel, spigot, and gasket positioning lug, see Figs. 1 and 2. ^B Dimensions D and F are laying lengths.


FIG. 28 Wye (corresponds to Table 39 of CISPI Specification 301)

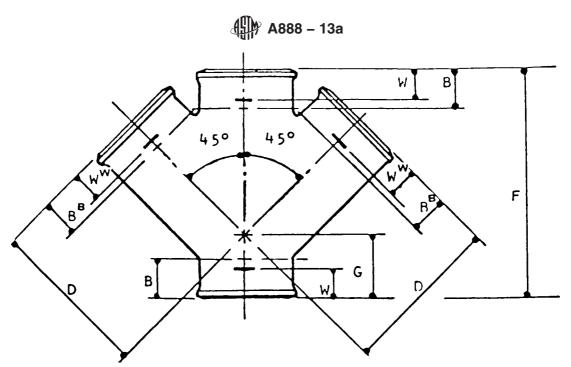

ASA Code Gro	up 022	Cina in			D	imensions, in. (mm	1) ^A		
Item No.		- Size, in.	В	B ^B	D ^B ±1/8 (3.2)	F ^B ±½ (3.2)	G	W	WW
1538	2	2	1½ (38)	1½ (38)	45% (117)	65/8 (168)	2 (51)	11/8 (29)	11/8 (29)
1540	8	3 by 2	11/2 (38)	1½ (38)	55/16 (135)	65/8 (168)	1½ (38)	11/8 (29)	11/8 (29)
1542	4	3	11/2 (38)	1½ (38)	53/4 (146)	8 (203)	21/4 (57)	11/8 (29)	11/8 (29)
1544	0	4 by 2	11/2 (38)	1½ (38)	6 (152)	65/8 (168)	1 (25)	11/8 (29)	11/8 (29)
1546	5	4 by 3	11/2 (38)	1½ (38)	6½ (165)	8 (203)	111/16 (43)	11/8 (29)	11/8 (29)
1548	1	4	11/4 (32)	1½ (38)	71/16 (179)	91/2 (241)	27/16 (62)	11/8 (29)	11/8 (29)
1550	7	5 by 4	2 (51)	1½ (38)	81/2 (216)	113/16 (284)	27/16 (62)	11/2 (38)	11/8 (29)
1552	3	6 by 4	2 (51)	1½ (38)	91/4 (235)	113/16 (284)	115/16 (49)	1½ (38)	11/8 (29)
1554	9	6	2 (51)	2 (51)	10¾ (273)	141/16 (357)	35/16 (84)	1½ (38)	1½ (38)
1556	3	8 by 4	21/2 (64)	21/4 (57)	10% (264)	117/16 (291)	15/16 (24)	2 (51)	11/8 (29)
1557	1	8 by 6	2½ (64)	23/4 (70)	1113/16 (300)	143/16 (360)	25/16 (59)	2 (51)	1½ (38)
1558	0	8	21/2 (64)	31/4 (83)	13% (340)	171/8 (435)	33/4 (95)	2 (51)	2 (51)

^A For details of barrel, spigot, and gasket positioning lug, see Figs. 1 and 2. ^B Dimensions D and F are laying lengths.


FIG. 29 Double Wye (corresponds to Table 42 of CISPI Specification 301)

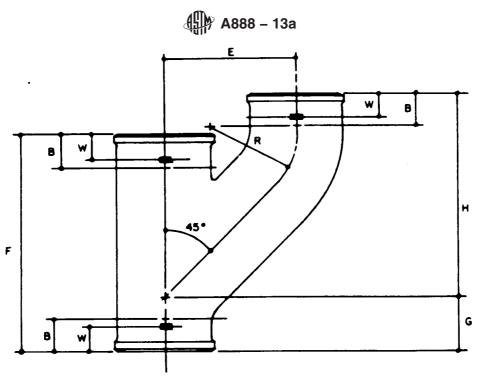

ASA Code Gr	oup 022	— Size, in.				Dimensions, in. (n	nm) ^A		
Item No.	$\sqrt{}$	— Size, III.	В	Н	E	F ^B (±1/8)	G	R	W
1646	3	2	1½ (38)	81/4 (210)	5½ (140)	7 (178)	2 (51)	3 (76)	11/8 (29)
1648	9	3 by 2	1½ (38)	83/16 (208)	5½ (140)	7 (178)	11/2 (38)	3 (76)	11/8 (29)
1650	5	3	1½ (38)	87/16 (214)	5½ (140)	83/8 (86)	23/16 (56)	3½ (89)	11/8 (29)
1652	1	4 by 2	1½ (38)	81/4 (210)	5½ (140)	7 (178)	1 (25)	3 (76)	11/8 (29)
1654	7	4 by 3	1½ (38)	87/16 (214)	5½ (140)	83/8 (86)	111/16 (43)	3½ (89)	11/8 (29)
1656	2	4	1½ (38)	91/8 (232)	6 (152)	93/4 (248)	27/16 (62)	4 (102)	11/8 (29)
1658	4	5 by 2	1½ (38)	9 (229)	63/4 (171)	8 (203)	2 (51)	3 (76)	1½ (38)
1660	8	5 by 3	1½ (38)	81/4 (210)	61/4 (159)	95/8 (244)	2% (60)	31/2 (89)	1½ (38)
1662	6	5	1½ (38)	117/16 (291)	71/8 (181)	1211/16 (322)	23/4 (70)	41/2 (114)	1½ (38)

^A For details of barrel, spigot, and gasket positioning lug, see Figs. 1 and 2. ^B Dimension F is laying length.


FIG. 30 Upright Wye (corresponds to Table 45 of CISPI Specification 301)

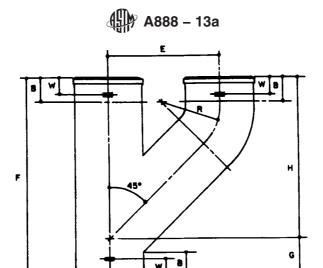

ASA Code Gr	oup 022	— Size, in.			[Dimensions, in. (m	m) ^A		
Item No.		— Size, III.	В	Н	E	F ^B ±1/8 (3.2)	G	R	W
022 9003	4	3 by 2						31/2 (89)	11/8 (29)
022 9000	5	3 by 3	1½ (38)	10 (254)	7 (178)	121/4 (311)	21/4 (57)	31/2 (89)	11/8 (29)
022 9004	6	4 by 2							11/8 (29)
022 9001	3	4 by 3	1½ (38)	10 (254)	7 (178)	1111/16 (297)	111/16 (43)	31/2 (89)	11/8 (29)
022 9002	1	4 by 4	1½ (38)	101/8 (257)	7 (178)	129/16 (319)	27/16 (62)	4 (102)	11/8 (29)

^A For details of barrel, spigot, and gasket positioning lug, see Figs. 1 and 2. ^B Dimensions F is laying length.

FIG. 31 Upright Wye Wide Center—Florida Special (corresponds to Table 46 of CISPI Specification 301)

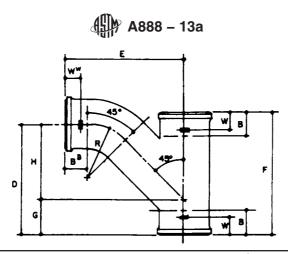

ASA Co							Dimensions,	in. (mm) ^A				
Group 0	22	Size, in.										
Item No.		Size, III.	В	$B^{\mathcal{B}}$	D	E ^B ±½ (3.2)	F ^B ±½ (3.2)	G	Н	R	W	WW
1694	3	11/2	1½ (38)	1½ (38)	4¾ (121)	5% (137)	6 (152)	2 (51)	23/4 (70)	23/4 (70)	11/8 (29)	11/8 (29)
1696	8	2 by 11/2	1½ (38)	11/2 (38)	5 (127)	5% (149)	6 (152)	2 (51)	3 (76)	23/4 (70)	11/8 (29)	11/8 (29)
1698	4	2 3 by 1½	1½ (38)	1½ (38)	5% (137)	61/8 (156)	65/8 (168)	2 (51)	3% (86)	3 (76)	11/8 (29)	11/8 (29)
1700	8	3 by 2	1½ (38)	1½ (38)	5½ (140)	6¾ (171)	65/8 (168)	1½ (38)	4 (102)	3 (76)	11/8 (29)	11/8 (29)
1702		3	1½ (38)	1½ (38)	7 ⁵ / ₁₆ (186)	8 (203)	8 (203)	21/4 (57)	51/16 (129)	3½ (89)	11/8 (29)	11/8 (29)
1704		4 by 2	1½ (38)	1½ (38)	5½ (140)	71/4 (184)	65/8 (168)	1 (25)	4½ (114)	3 (76)	11/8 (29)	11/8 (29)
1706		4 by 3	1½ (38)	1½ (38)	71/4 (184)	8½ (216)	8 (203)	111/16 (49)	5%16 (141)	3½ (89)	11/8 (29)	11/8 (29)
1708	1	4	1½ (38)	1½ (38)	91/4 (235)	10 (254)	9½ (241)	27/16 (62)	613/16 (173)	4 (102)	11/8 (29)	11/8 (29)
1710	-	5 by 2	2 (51)	1½ (38)	5 ¹⁵ / ₁₆ (151)	73/4 (197)	81/16 (205)	15/16 (24)	5 (127)	3 (76)	1½ (38)	11/8 (29)
1712		5 by 3	2 (51)	1½ (38)	73/4 (197)	9 (229)	911/16 (246)	111/16 (43)	61/16 (154)	3½ (89)	1½ (38)	11/8 (29)
1714	9	5 by 4	2 (51)	1½ (38)	93/4 (248)	10½ (267)	113/16 (284)	27/16 (62)	75/16 (186)	4 (102)	1½ (38)	11/8 (29)
1716		5	2 (51)	2 (51)	113/4 (298)	12½ (318)	125/8 (321)	31/8 (79)	85/8 (219)	4½ (114)	1½ (38)	1½ (38)
1718		6 by 2	2 (51)	6 (152)	81/4 (210)	85/16 (211)	1/2 (13)	5½ (140)	3 (76)	1½ (38)	1½ (38)	11/8 (29)
1720		6 by 3	2 (51)	1½ (38)	713/16 (198)	9½ (241)	93/4 (248)	11/4 (32)	6% ₁₆ (167)	3½ (89)	1½ (38)	11/8 (29)
1722		6 by 4	2 (51)	1½ (38)	93/4 (248)	11 (279)	113/16 (284)	115/16 (49)	713/16 (198)	4 (102)	1½ (38)	11/8 (29)
1724		6 by 5	2 (51)	2 (51)	1111/16	13 (330)	12½ (318)	29/16 (65)	91/8 (232)	4½ (114)	1½ (38)	1½ (38)
1726	3		2 (51)	2 (51)	135/8 (346)	14% (365)	141/16 (357)	35/16 (84)	105/16 (262)	5 (127)	1½ (38)	1½ (38)
1728		8 by 4	2½ (64)	1½ (38)	97/16 (240)	115/16 (287)	113/16 (284)	⁷ / ₈ (22)	8%16 (217)	4 (102)	2 (51)	11/8 (29)
1730		8 by 5	21/2 (64)	2 (51)	10 ¹⁵ / ₁₆ (278)	1213/16 (325)	1211/16 (322)	15/8 (41)	95/16 (237)	4½ (114)	2 (51)	1½ (38)
1732	1	8 by 6	2½ (64)	2 (51)	12 (305)	13% (340)	1315/16 (354)	21/4 (57)	93/4 (248)	5 (127)	2 (51)	1½ (38)
1734	7	8	2½ (64)	21/2 (64)	14¾ (375)	15% (395)	16 ¹⁵ / ₁₆ (430)	3¾ (95)	11 (279)	6 (152)	2 (51)	2 (51)
						Extend	led Pattern					
ASA Co Group 0							Dimensions,	in. (mm) ^A				
		Size, in.				E ^B	F ^B					
Item No.			В	B^B	D	± ¹ / ₈ (3.2)	±½ (3.2)	G	Н	R	W	WW
1738	1	11/2	2	1½ (38)	16¾ (425)	61/8 (156)	18 (457)	13% (340)	3% (86)	3 (76)	11/8 (29)	11/8 (29)
1740	3	2 by 1½	2	1½ (38)	22¾ (578)	61/8 (156)	24 (610)	19% (492)	3% (86)	3 (76)	11/8 (29)	11/8 (29)

^A For details of barrel, spigot, and gasket positioning lug, see Figs. 1 and 2. ^B Dimensions E and F are laying lengths.

3 by 2

11/2 (38)

11/2 (38)

343/4 (883)

34 (864)

61/8 (156)

63/4 (171)

5 2

2 by 2 7 3 by 2

1742

1744

FIG. 32 Combination Wye and 1/8 Bend (corresponds to Table 47 of CISPI Specification 301)

36 (914)

36 (914)

263/4 (679)

30 (762)

3% (86)

4 (102)

3 (76)

3 (76)


11/8 (29)

11/8 (29)

11/8 (29)

11/8 (29)




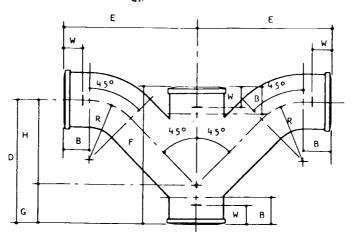

ASA Code 022		— Size, in.				Dim	ensions, in. (mm)	A		
Item No.	$\sqrt{}$	— Size, III.	В	D	E ^B ±1/8 (3.2)	F ^B ±½ (3.2)	G	Н	R	W
1802	2	2	1½ (38)	5% (137)	61/8 (156)	65/8 (168)	2 (51)	3% (86)	3 (76)	11/8 (29)
1804	8	3 by 2	11/2 (38)	5½ (140)	6¾ (171)	65/8 (168)	1½ (38)	4 (102)	3 (76)	11/8 (29)
1806	3	3	1½ (38)	75/16 (186)	8 (203)	8 (203)	21/4 (57)	51/16 (129)	3½ (89)	11/8 (29)
1808	9	4 by 2	1½ (38)	5½ (140)	71/4 (184)	65/8 (168)	1 (25)	41/2 (114)	3 (76)	11/8 (29)
1810	5	4 by 3	1½ (38)	71/4 (184)	81/2 (216)	8 (203)	111/16 (43)	5%16 (141)	3½ (89)	11/8 (29)
1812	1	4	1½ (38)	91/4 (235)	10 (254)	9½ (241)	27/16 (62)	613/16 (173)	4 (102)	11/8 (29)

^A For details of barrel, spigot, and gasket positioning lug, see Figs. 1 and 2. ^B Dimensions E and F are laying lengths.

FIG. 33 Combination Wye and 1/8 Bend, Double (corresponds to Table 50 of CISPI Specification 301)




ASA Code (022	Group	Size, in.			Dimensions, in. (mm) ^A					
Item No.	V	_	В	E ^B ±½ (3.2)	F ^B ±½ (3.2)	D	R	W	WW	W ^B
1850	1	11/2	1½ (38)	41/4 (108)	6½ (165)	41/4 (108)	23/4 (70)	11/8 (29)	11/8 (29)	1½ (38)
1852	7	2	1½ (38)	41/2 (114)	67/8 (175)	41/2 (114)	3 (76)	11/8 (29)	11/8 (29)	1½ (38)
1854	3	3 by 2	1½ (38)	5 (127)	6% (175)	41/2 (114)	3 (76)	11/8 (29)	11/8 (29)	1½ (38)
1856	8	3	1½ (38)	5 (127)	8 (203)	5 (127)	31/2 (89)	11/8 (29)	11/8 (29)	1½ (38)
1958	4	4 by 2	1½ (38)	5½ (140)	67/8 (175)	41/2 (114)	3 (76)	11/8 (29)	11/8 (29)	1½ (38)
1860	0	4 by 3	1½ (38)	51/2 (140)	8 (203)	5 (127)	31/2 (89)	11/8 (29)	11/8 (29)	1½ (38)
1862	6	4	1½ (38)	51/2 (140)	91/8 (232)	5½ (140)	4 (102)	11/8 (29)	11/8 (29)	1½ (38)
		5 by 4	, ,	6	1013/326	, ,	, ,	, ,	, ,	, ,
1868	3	6 by 2	2 (51)	61/2 (165)	83/16 (208)	5 (127)	3 (76)	1½ (38)	11/8 (29)	1½ (38)
1864	2	6 by 4	2 (51)	61/2 (165)	101/16 (256)	6 (152)	4 (102)	1½ (38)	11/8 (29)	1½ (38)
1867	5	6	2 (51)	7 (178)	121/2 (318)	7 (178)	5 (127)	1½ (38)	11/2 (38)	2 (51)
1874	1	8 by 4	21/2 (64)	7½ (191)	11½ (292)	6½ (165)	4 (102)	2 (51)	11/8 (29)	1½ (38)
1878	2	8	21/2 (64)	81/2 (216)	15½ (394)	81/2 (216)	6 (152)	2 (51)	2 (51)	21/2 (64)

^A For details of barrel, spigot, and gasket positioning lug, see Figs. 1 and 2. ^B Dimensions E and F are laying lengths.

FIG. 34 Sanitary Cross (corresponds to Table 51 of CISPI Specification 301)



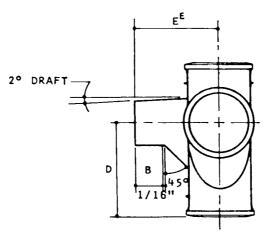


Note 1-Inclusion of spigot bead and positioning lug optional with manufacturer based on casting method used.

ASA Code 022		Size,	Dim	ensions, in. (mn	າ) ^{A,B}
Item No.	\checkmark	in.	В	E ^{EC} ±½ (3.2)	D
1898 1900	0 4	3 by 3 by 2 4 by 4 by 2	1½ (38) 1½ (38)	4 ⁷ / ₁₆ (113) 4 ¹⁵ / ₁₆ (125)	5 (127) 5½ (140)

A For details of barrel, spigot, and gasket positioning lug, see Figs. 1 and 2.

FIG. 35 Sanitary Cross With Side Opening (corresponds to Table 52 of CISPI Specification 301)

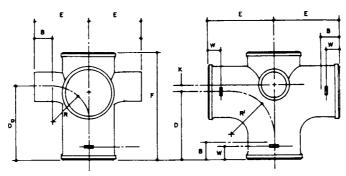

Note 1-Inclusion of spigot bead and positioning lug optional with manufacturer based on casting method used.


ASA Co Group 0		Size, in.				Г	Dimensions, in. ((mm) ^A				
Item No.	\checkmark	Size, III.	В	E ^{EB} ±1/8 (3.2)	E ^B ±½ (3.2)	F ^B ±1/8 (3.2)	D	D^D	K	R	R'	W
1982	2	3 by 3 by 2	1½ (38)	41/2 (114)	5 (127)	81/2 (216)	5 (127)	6 (152)	1 (25)	3 (76)	3½ (89)	11/8 (29)
1984	8	4 by 4 by 2	1½ (38)	5 (127)	5½ (140)	91/8 (232)	5½ (140)	6½ (165)	1 (25)	3 (76)	4 (102)	11/8 (29)

^A For details of barrel, spigot, and gasket positioning lug, see Figs. 1 and 2. ^B Dimensions E, F, and E^E are laying lengths.

FIG. 36 Sanitary Cross With Side Openings Above Center (New Orleans) (corresponds to Table 55 of CISPI Specification 301)

^B For details of sanitary cross, see Fig. 34.
^C Dimension E^E is laying length.



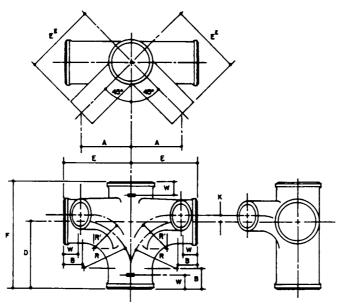


Note 1—Inclusion of spigot bead and positioning lug shall be optional with manufacturer based on casting method used. Note 2—For details of sanitary cross, see Fig. 34.

ASA Co Group		Size, in.]	Dimensions,	in. (mm) ^A					
Item No.	$\sqrt{}$	Size, III.	Α	В	E ^{EB} ±1/8 (3.2)	$E^B \pm \frac{1}{8}$ (3.2)	F ^B ±½ (3.2)	F ^B N.O.	D	K	K N.O.	R	R'	W
1994	7	3 by 3 by 2	3¾ (95)	11/2 (38)	5% (137)	5 (127)	8 (203)	81/2 (216)	5 (127)	1 (25)	1 (25)	31/2 (89)	3 (76)	11/8 (29)
2000	2	4 by 4 by 2	45/16 (110)	11/2 (38)	61/8 (156)	5½ (140)	91/8 (232)	91/8 (232)	5½ (140)	1/2 (13)	1 (25)	4 (102)	3 (76)	11/8 (29)

A For details of barrel, spigot, and gasket positioning lug, see Figs. 1 and 2. B Dimensions E, F, and E^E are laying lengths.

FIG. 37 Sanitary Cross With Two 45° Side Openings on Same Side (Regular and New Orleans Special) (corresponds to Table 56 of CISPI Specification 301)

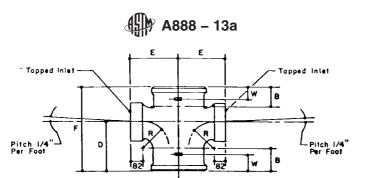


ASA Code Gro	oup 022	Cina in			D	imensions, in. (mm) ^A		
Item No.		 Size, in. 	В	E	F ^B ±½ (3.2)	D	R	IPS Tapping ^C	W
2012	7	1½ by 1½	11/2 (38)	29/16 (65)	511/16 (144)	31/4 (83)	13/4 (44)	1½ (38)	11/8 (29)
2014	3	2 by 11/4	1½ (38)	213/16 (71)	511/16 (144)	31/4 (83)	13/4 (44)	11/4 (32)	11/8 (29)
2016	8	2 by 1½	1½ (38)	213/16 (71)	511/16 (144)	31/4 (83)	13/4 (44)	1½ (38)	11/8 (29)
2018	4	2 by 2	1½ (38)	31/16 (78)	63/8 (162)	33/4 (95)	21/4 (57)	2 (51)	11/8 (29)
2020	0	3 by 11/4	1½ (38)	35/16 (84)	511/16 (144)	31/4 (83)	13/4 (44)	11/4 (32)	11/8 (29)
2022	6	3 by 1½	1½ (38)	35/16 (84)	511/16 (144)	31/4 (83)	13/4 (44)	1½ (38)	11/8 (29)
2024	2	3 by 2	1½ (38)	39/16 (90)	63/8 (162)	33/4 (95)	21/4 (57)	2 (51)	11/8 (29)
2026	7	4 by 11/4	1½ (38)	313/16 (97)	511/16 (144)	31/4 (83)	13/4 (44)	11/4 (32)	11/8 (29)
2028	3	4 by 1½	1½ (38)	313/16 (97)	511/16 (144)	31/4 (83)	13/4 (44)	1½ (38)	11/8 (29)
2030	9	4 by 2	1½ (38)	41/16 (103)	63/8 (162)	33/4 (95)	21/4 (57)	2 (51)	11/8 (29)
		5 by 1½	, ,	, ,	, ,		, ,	• •	, ,
2034	1	6 by 1½	2 (51)	413/16 (122)	611/16 (170)	33/4 (95)	13/4 (44)	1½ (38)	1½ (38)
2036	6	6 by 2	2 (51)	51/16 (129)	77/16 (189)	41/4 (108)	21/4 (57)	2 (51)	11/2 (38)
				Ext	ended Patterns				
ASA Code Gro	oup 022	- Size in			1	Dimensions, in.	(mm) ^A		
		- aize. III.							


ASA Code Gro	up 022	- Size. in.	Dimensions, in. (mm) ^A										
Item No.	\vee	- Size, III.	В	E	F ^B ±½ (3.2)	D	R	IPS Tapping $^{\mathcal{C}}$	W				
2038	9	2 by 1½ by 22%	11/2 (38)	213/16 (71)	227/8 (581)	3%	13/4 (44)	1½ (38)	11/8 (29)	_			
2040	3	2 by 1½ by 31	11/2 (38)	213/16 (71)	31 (787)	33/8	13/4 (44)	1½ (38)	11/8 (29)				
2041	4	2 by 2 by 221/8	11/2 (38)	31/16 (78)	227/8 (581)		21/4 (57)	2 (51)	11/8 (29)				
2042	5	2 by 2 by 31	11/2 (38)	31/16 (78)	31 (787)	33/8	21/4 (57)	2 (51)	11/8 (29)				

^A For details of barrel, spigot, and gasket positioning lug, see Figs. 1 and 2. ^B Dimension F is laying length. ^C For details of tapping bosses, see Fig. 58.

FIG. 38 Sanitary Cross, Tapped (corresponds to Table 57 of CISPI Specification 301)



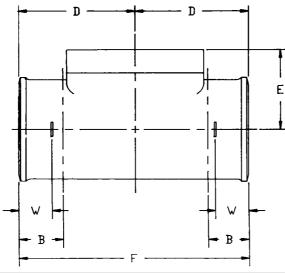




ASA Code Gro	oup 022	Size,	Dimensions, in. (mm) ^A									
Item No.		in.	В	E	F ^B ±½ (3.2)	D	IPS Tapping C	W				
2046	5	2	1½ (38)	2 (51)	63/8 (162)	33/16 (81)	2 (51)	11/8 (29)				
2048	1	3	1½ (38)	211/16 (68)	73/4 (197)	37/8 (98)	3 (76)	11/8 (29)				
8278	8	4	1½ (38)	3 (76)	87/8 (225)	47/16 (113)	31/2 (89)	11/8 (29)				
2050	7	4	11/2 (38)	3 (76)	87/8 (225)	47/16 (113)	4 (102)	11/8 (29)				
2052	3	5	2 (51)	4½ (114)	11½ (292)	53/4 (146)	5 (127)	1½ (38)				
2054	9	6	2 (51)	5 (127)	12½ (318)	61/4 (159)	6 (152)	1½ (38)				
2056	4	8	2 (51)	6 (152)	15½ (387)	75/8 (194)	8 (203)	2 (51)				
2058	0	10	4 (102)	6½ (165)	20 (508)	10 (254)	10 (254)	2 (51)				

^A For details of barrel, spigot, and gasket positioning lug, see Figs. 1 and 2. ^B Dimension F is laying length. ^C For details of tapping bosses, see Fig. 58.


FIG. 39 Test Tee (corresponds to Table 58 of CISPI Specification 301)

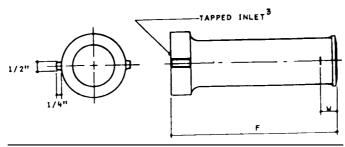

ASA Code (022	Group)	Size, in.	Dime	ensions, in. (mm) ^A
Item No.		-	Size, III.	F ^B ±½ (3.2)	IPS c Tapping $\sqrt{}$	W
2100	0	3		12 (305)	3 (76)	11/8 (29)

^A For details of barrel, spigot, and gasket positioning lug, see Figs. 1 and 2. ^B Dimension F is laying length. ^C For details of tapping bosses, see Fig. 58.

FIG. 40 Tapped Extension Piece (corresponds to Table 62 of CISPI Specification 301)

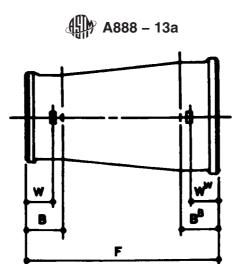


ASA Code Gro	oup 022	Cino in			Dimensions, in. (mm) ^A		
Item No.		Size, in.	В	B ^B	F ^B ±½ (3.2)	W	WW
2124	0	2 by 3	1½ (38)	1½ (38)	8 (203)	11/8 (29)	11/8 (29)
2126	5	2 by 4	1½ (38)	1½ (38)	8 (203)	11/8 (29)	11/8 (29)
		3 by 1½					
2128	1	3 by 4	1½ (38)	1½ (38)	8 (203)	11/8 (29)	11/8 (29)

^A For details of barrel, spigot, and gasket positioning lug, see Figs. 1 and 2. ^B Dimension F is laying length.

FIG. 41 Increaser-Reducer (corresponds to Table 63 of CISPI Specification 301)



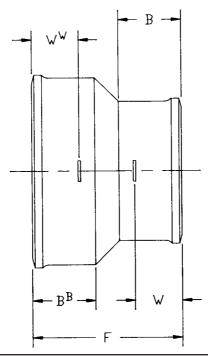


ASA Code Gro	oup 022	0: :-			Dimensions, in. (mm	n) ^A	
Item No.	V	— Size, in.	B, Minimum	B ^B , Minimum	F ^B ±½ (3.2)	W	WW
2138	0	2 by 1½	1½ (38)	1½ (38)	35/8 (92)	11/8 (29)	11/8 (29)
2140	6	3 by 2	11/2 (38)	11/2 (38)	35/8 (92)	11/8 (29)	11/8 (29)
2142	2	4 by 2	11/2 (38)	11/2 (38)	35/8 (92)	11/8 (29)	11/8 (29)
2144	8	4 by 3	11/2 (38)	11/2 (38)	35/8 (92)	11/8 (29)	11/8 (29)
2146	3	5 by 2	1½ (38)	2 (51)	4 (102)	11/8 (29)	1½ (38)
2148	9	5 by 3	1½ (38)	2 (51)	4 (102)	11/8 (29)	1½ (38)
2150	5	5 by 4	11/2 (38)	2 (51)	4 (102)	11/8 (29)	1½ (38)
2152	1	6 by 2	11/2 (38)	2 (51)	4 (102)	11/8 (29)	1½ (38)
2154	7	6 by 3	11/2 (38)	2 (51)	4 (102)	11/8 (29)	1½ (38)
2156	2	6 by 4	11/2 (38)	2 (51)	4 (102)	11/8 (29)	1½ (38)
2158	8	6 by 5	2 (51)	2 (51)	4½ (114)	11/2 (38)	1½ (38)
2160	4	8 by 2	1½ (38)	2 (51)	41/2 (114)	11/8 (29)	2 (51)
2162	0	8 by 3	11/2 (38)	2 (51)	41/2 (114)	11/8 (29)	2 (51)
2164	6	8 by 4	11/2 (38)	2 (51)	41/2 (114)	11/8 (29)	2 (51)
2166	1	8 by 5	2 (51)	2 (51)	5 (127)	11/2 (38)	2 (51)
2168	7	8 by 6	2 (51)	2 (51)	5 (127)	11/2 (38)	2 (51)
2172	9	10 by 4	1½ (38)	3 (76)	5½ (140)	11/8 (29)	2 (51)
2174	5	10 by 6	2 (51)	3 (76)	6 (152)	11/2 38)	2 (51)
2175	2	10 by 8	2 (51)	3 (76)	6 (152)	2 (51)	2 (51)
2176	0	12 by 4	1 ½ (38)	3 1/4 (83)	6 ½ (165)	1 1/8 (29)	2 3/4 (70)
2177	3	12 by 6	2 (51)	3 1/4 (83)	6 ½ (165)	1 ½ (38)	2 3/4 (70)
2178	9	12 by 8	2 ½ (64)	3 1/4 (83)	7 (178)	2 (51)	2 3/4 (70)
2179	6	12 by 10	3 (76)	3 1/4 (83)	7 ½ (191)	2 (51)	2 3/4 (70)
2180	8	15 by 4	1 ½ (38)	3 1/4 (83)	7 (178)	1 1/8 (29)	2 ¾ (70)
2181	4	15 by 6	2 (51)	3 1/4 (83)	7 (178)	1 ½ (38)	2 3/4 (70)
2182	7	15 by 8	2 ½ (64)	3 1/4 (83)	7 (178)	2 (51)	2 3/4 (70)
2183	1	15 by 10	3 (76)	3 1/4 (83)	7 ½ (191)	2 (51)	2 3/4 (70)
2184	2	15 by 12	3 1/4 (83)	3 1/4 (83)	7 3/4 (197)	2 3/4 (70)	2 3/4 (70)

^A For details of barrel, spigot, and gasket positioning lug, see Figs. 1 and 2. ^B Dimension F is laying length.

FIG. 42 Short, Increaser-Reducer (corresponds to Table 64 of CISPI Specification 301)



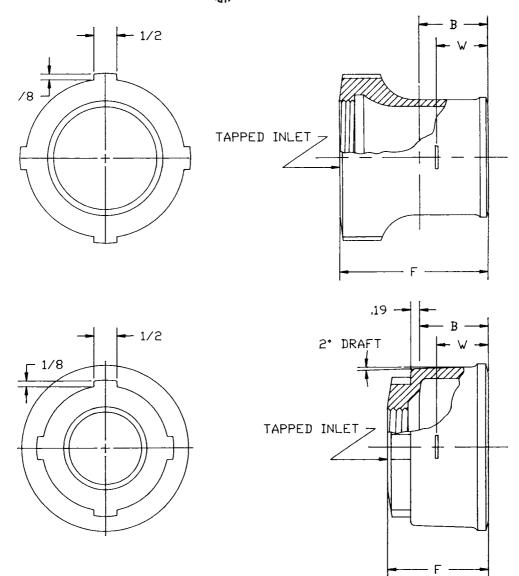

ASA Code Group 022		Oine in	Dimensions, in. (mm) ^A							
Item No.	V	— Size, in.	В	F	IPS Tapping ^B	Mc				
2236	2	1½ by 1¼	1½ (38)	25/8 (67)	11/4 (32)	11/8 (29)				
2238	8	1½ by 1½	11/2 (38)	25/8 (67)	11/2 (38)	11/8 (29)				
2240	4	2 by 11/4	11/2 (38)	23/16 (56)	11/4 (32)	11/8 (29)				
2242	0	2 by 1½	1½ (38)	23/16 (56)	1½ (38)	11/8 (29)				
2244	6	2 by 2	1½ (38)	25/8 (67)	2 (51)	11/8 (29)				
2246	1	3 by 11/4	11/2 (38)	23/16 (56)	11/4 (32)	11/8 (29)				
2248	7	3 by 1½	11/2 (38)	23/16 (56)	11/2 (38)	11/8 (29)				
2250	3	3 by 2	1½ (38)	23/16 (56)	2 (51)	11/8 (29)				
2252	9	3 by 21/2	11/2 (38)	23/16 (56)	2½ (64)	11/8 (29)				
2254	5	4 by 31/2	11/2 (38)	23/16 (56)	3½ (89)	11/8 (29)				
2259	4	5 by 4	2 (51)	4½ (114)	4 (102)	1½ (38)				
2262	8	6 by 5	2 (51)	4½ (114)	5 (127)	1½ (38)				
2274	3	8 by 6	2 (51)	4½ (114)	6 (152)	2 (51)				


FIG. 43 Tapped Adapters (corresponds to Table 65 of CISPI Specification 301)

^A For details of barrel, spigot, and gasket positioning lug, see Figs. 1 and 2.

^B For details of tapping bosses, see Fig. 58.


^C Inclusion of spigot bead and positioning lug optional with manufacturer based on casting method used.



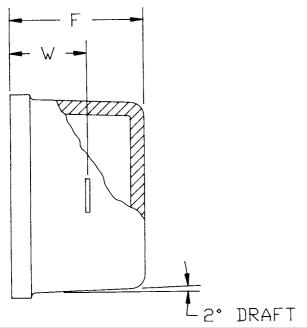

ASA Code G	Group	Size,	Dimensions, in. $(mm)^A$				
Item No.		in.	F ^B ±1/8 (3.2)	W ^C			
2480	6	11/2	13/4 (44)	11/8 (29)			
2482	2	2	13/4 (44)	11/8 (29)			
2484	8	3	13/4 (44)	11/8 (29)			
2486	3	4	13/4 (44)	11/8 (29)			
2488	9	5	13/4 (44)	11/2 (38)			
2490	5	6	13/4 (44)	11/2 (38)			
2492	1	8	21/4 (57)	2 (51)			
2494	7	10	3 (76)	2 (51)			
2495	7	12	3 ½ (89)	2 3/4 (70)			
2496	7	15	3 ½ (89)	2 3/4 (70)			

FIG. 44 Blind Plug (corresponds to Table 66 of CISPI Specification 301)

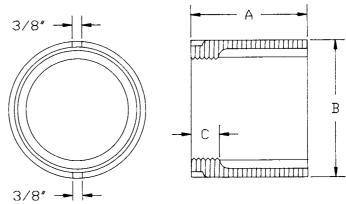

Note 1-Inclusion of spigot bead positioning lug optional with manufacturer based on casting method used.

ASA Code C	iroup	Size,		Dimension)^A	
Item No.		in.	Α	В	С	IPS Tapping ^B
8562	3	2	23/16 (56)	23/8 (60)	3/4 (19)	1½ (38)
8564	1	3	23/16 (56)	3% (86)	3/4 (19)	21/2 (64)
8566	6	4	23/16 (56)	47/16 (113)	3/4 (19)	31/2 (89)
8568	2	5	41/2 (114)	55/16 (135)	1 (25)	4 (102)
8570	8	6	41/2 (114)	65/16 (160)	1 (25)	5 (127)
8572	4	8		8% (213)		6 (152)

^A For details of barrel and spigot, see Figs. 1 and 2.

FIG. 45 Iron Body Cleanout-Tapped (corresponds to Table 67 of **CISPI Specification 301)**


^A For details of barrel and spigot, see Figs. 1 and 2.

^B Dimension F is laying length.

^C Inclusion of spigot bead and positioning lug optional with manufacturer based on casting method used.

^B For details of tapping bosses, see Fig. 58.



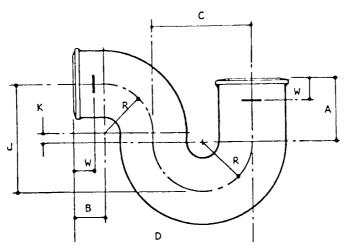


Note 1—A minimum water seal of 2 in. (51 mm) is provided for 2-in. size and smaller, 21/2 in. (64 mm) for sizes 3 to 6 in. inclusive.

ASA Code (022	Group	Size, in.	Dimensions, in. (mm) ^A							
Item No.		_ `	Α	В	С	D ^B ±1/8 (3.2)	J	K	R	W
2506	8	11/2	2 (51)	1½ (38)	3½ (89)	6¾ (171)	31/2 (89)		13/4 (44)	11/8 (29)
2508	4	2	2 (51)	1½ (38)	4 (102)	7½ (191)	4 (102)		2 (51)	11/8 (29)
2510	0	3	31/4 (83)	11/2 (38)	5 (127)	9 (229)	5½ (140)	1/2 (13)	21/2 (64)	11/8 (29)
2512	6	4	4 (102)	1½ (38)	6 (152)	10½ (267)	6½ (165)	1/2 (13)	3 (76)	11/8 (29)
2514	2	6	6 (152)	2 (51)	8 (203)	14 (356)	81/2 (216)	1/2 (13)	4 (102)	1½ (38)

^A For details of barrel, spigot, and gasket positioning lug, see Figs. 1 and 2.

FIG. 46 P Trap (corresponds to Table 68 of CISPI Specification 301)

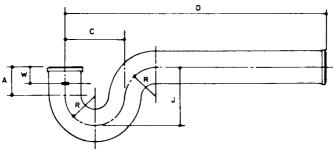

Note 1—A minimum water seal of 2 in. (51 mm) is provided for 2-in. size and smaller


ASA Code C	ASA Code Group 022				Dimensions,	, in. (mm) ^A		
Item No.	√	— Size, in.	А	С	D ^B ±1/8 (3.2)	J	R	W
2527	4	2 by 12	2 (51)	4 (102)	12 (305)	4 (102)	2 (51)	11/8 (29)
2528	2	2 by 14	2 (51)	4 (102)	14 (356)	4 (102)	2 (51)	11/8 (29)
2529	0	2 by 16	2 (51)	4 (102)	16 (406)	4 (102)	2 (51)	11/8 (29)
2530	8	2 by 18	2 (51)	4 (102)	18 (457)	4 (102)	2 (51)	11/8 (29)

 $^{^{\}it A}$ For details of barrel, spigot, and gasket positioning lug, see Figs. 1 and 2.

FIG. 47 Long P Trap (corresponds to Table 69 of CISPI Specification 301)

 $^{^{\}it B}$ Dimension D is laying length.


^B Dimension D is laying length.

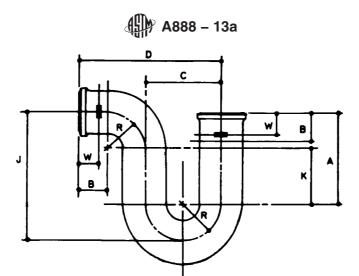

ASA Code		Size, in.		Dimensions, in. (mm) ^A							
Item No.		-	Α	В	С	D ^B ±1/8 (3.2)	K	J	R	W	Seal
2564	7	2	5 (127)	1½ (38)	4 (102)	7½ (191)	3 (76)	7 (178)	2 (51)	11/8 (29)	5 (127)
2566	2	3	41/2 (114)	1½ (38)	5 (127)	9 (229)	2 (51)	7 (178)	21/2 (64)	11/8 (29)	4 (102)
2567	0	4	5 (127)	1½ (38)	6 (152)	10½ (267)	2 (51)	8 (203)	3 (76)	11/8 (29)	4 (102)

^A For detail of barrel, spigot, and gasket positioning lug, see Figs. 1 and 2.

FIG. 48 Deep Seal P Trap (corresponds to Table 71 of CISPI Specification 301)

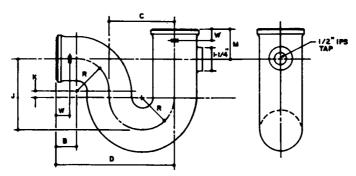

Note 1—A minimum water seal of 2 in. (51 mm) is provided for 2-in. size and smaller, 21/2 in. (64 mm) for sizes 3 to 4 in. inclusive.

ASA Code 022		- Size, in.	Dimensions, in. (mm) ^A									
Item No.	\checkmark	Size, III.	Α	В	С	D ^B ±½ (3.2)	J	K	R	W	М	IPS Tapping ^C
8530	2	2	2 (51)	1½ (38)	4 (102)	7½ (191)	4 (102)	0 (0)	2 (51)	11/8 (29)	2 (51)	1/2 (13)
8532	8	3	31/4 (83)	1½ (38)	5 (127)	9 (229)	5½ (140)	1/2 (13)	21/2 (64)	11/8 (29)	2 (51)	1/2 (13)
8534	4	4	4 (102)	1½ (38)	6 (152)	10½ (267)	6½ (165)	1/2 (13)	3 (76)	11/8 (29)	2 (51)	1/2 (13)


^A For details of barrel, spigot, and gasket positioning lug, see Figs. 1 and 2. ^B Dimension D is laying length.

FIG. 49 P Trap with Primer (corresponds to Table 73 of CISPI Specification 301)

^B Dimension D is laying length.

^C Minimum thickness of threaded section of primer tap is 0.21 in. (5.3 mm).



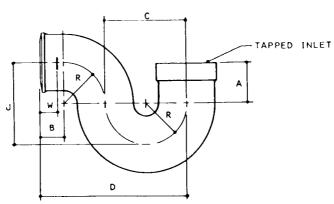


Note 1—A minimum water seal of 2 in. (51 mm) is provided for 2-in. size and smaller.

ASA Code Group 022		Ci=o in				Dimensio	ns, in. (mm) ^A			
Item No.	$\sqrt{}$	Size, in.	A	В	С	D ^B ±1/8 (3.2)	J	R	IPS Tapping ^C	W
2582	9	1½ by 1½	2 (51)	1½ (38)	3½ (89)	63/4 (171)	31/2 (89)	13/4 (44)	1½ (38)	11/8 (29)
2586	0	2 by 1½	2 (51)	1½ (38)	4 (102)	7½ (191)	4 (102)	2 (51)	1½ (38)	11/8 (29)
2588	6	2 by 2	2 (51)	1½ (38)	4 (102)	7½ (191)	4 (102)	2 (51)	2 (51)	11/8 (29)

A For details of barrel, spigot, and gasket positioning lug, see Figs. 1 and 2.

FIG. 50 P Trap With Tapped Inlet (corresponds to Table 74 of CISPI Specification 301)

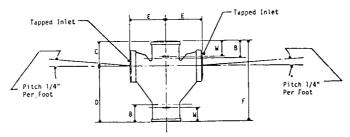

ASA Code Gro	oup 022	Size, in.			Di	mensions, in. (mm)	A		
Item No.	\vee	Size, III.	В	С	D	F ^B ±½ (3.2)	E	IPS Tapping $^{\mathcal{C}}$	W
8002	2	2 by 2 by 1½ by 1½	1½ (38)	21/8 (54)	47/8 (124)	7 (178)	33/16 (81)	1½ (38)	11/8 (29)

^A For details of barrel, spigot, and gasket positioning lug, see Figs. 1 and 2.


FIG. 51 Tapped Inlet, Double (corresponds to Table 76, Fig. 1A of CISPI Specification 301)

^B Dimension D is laying length.

^C For details of tapping bosses, see Fig. 58.

B Dimension F is laying length.


C For details of tapping bosses, see Fig. 58.

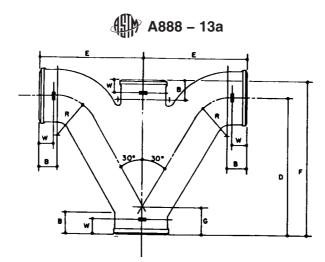

ASA Code Gro	oup 022	Cino in	Dimensions, in. (mm) ^A						
Item No.	\checkmark	Size, in.	В	D	E ^B ±1/8 (3.2)	F ^B ±1/8 (3.2)	G	R	W
8052	7	2	1½ (38)	6½ (165)	5 (127)	8 (203)	113/16 (46)	1% (35)	11/8 (29)
8054	3	3 by 2 by 3	1½ (38)	87/8 (225)	6%16 (167)	91/4 (235)	2 (51)	21/2 (64)	11/8 (29)
8058	4	4 by 2 by 4	1½ (38)	101/4 (260)	73/4 (197)	11½ (292)	115/16 (49)	3 (76)	11/8 (29)
8062	6	4	1½ (38)	101/4 (260)	73/4 (197)	12 (305)	115/16 (49)	3 (76)	11/8 (29)

^A For details of barrel, spigot, and gasket positioning lug, see Figs. 1 and 2. ^B Dimensions E and F are laying lengths.


FIG. 52 Modified Combination Wye and 1/8 Bend, Double (corresponds to Table 80, Fig. 5 of CISPI Specification 301)

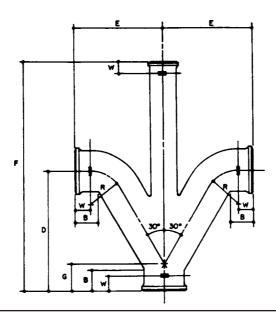


ASA Code Gr	oup 022	- Size, in.	Dimensions, in. (mm) ^A							
Item No.	\checkmark	Size, III.	E ^B ±1/8 (3.2)	В	F ^B ±½ (3.2)	G	D	R	W	
8088	1	3 by 2 by 3	6%16 (167)	1½ (38)	167/8 (429)	2 (51)	87/8 (225)	21/2 (64)	11/8 (29)	

 $^{^{\}rm A}$ For details of barrel, spigot, and gasket positioning lug, see Figs. 1 and 2. $^{\rm B}$ Dimensions E and F are laying lengths.

FIG. 53 Modified Combination Wye and 1/8 Bend, Double, Extended (corresponds to Table 80, Fig. 5, Extended, of CISPI Specification 301)

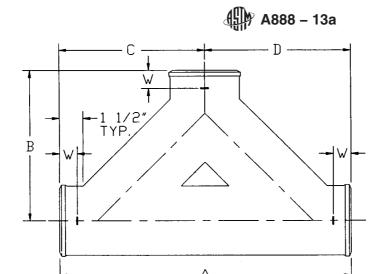




TYPICAL 4 X 3 TRANSITION

ASA Code Gro	ASA Code Group 022			Dimensions, in. (mm)						
Item No.	\checkmark	Size, in.	Α	В	С	D	W			
8442	0	3 by 3 by 4	15 (381)	9 (229)	7½ (191)	7½ (91)	11/8 (29)			
8444	6	4 by 3 by 4	19½ (495)	9½ (241)	93/16 (233)	101/4 (260)	11/8 (29)			
8446	1	4 by 4 by 4	18% (467)	9½ (241)	93/16 (233)	93/16 (233)	11/8 (29)			


FIG. 54 Two-Way Cleanout (corresponds to Table 87 of CISPI Specification 301)

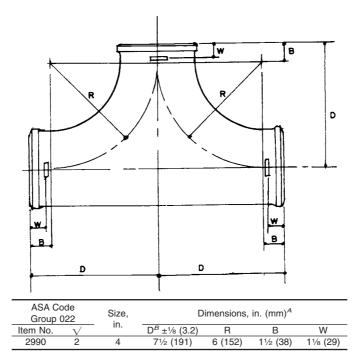

^A For details of barrel, spigot, and gasket positioning lug, see Figs. 1 and 2. ^B Dimension D is laying length.

FIG. 55 Twin Cleanout (corresponds to Table 88 of CISPI Specification 301)



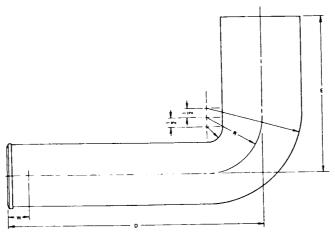

Note 1—Inclusion of spigot bead and positioning lug optional with manufacturer, based on casting method used.


Note 2—Inclusion of breaking rings on inlet end optional.

Size, in.,		Dimensi	ons in in.	
Availability ^A	D	E	R1	R2
3 by 4O	15	6		
3 by 4O	12	6		
3 by 4O	18	6		
3 by 4O	12	10		
3 by 4O	15	10		
3 by 4O	16	10		
3 by 4O	16	12		
3 by 4O	16	16		
4 by 4O	15	6		
4 by 4O	12	6		
4 by 4O	16	6		
4 by 4O	18	6		
4 by 4O	12	10		
4 by 4O	15	10		
4 by 4O	16	10		
4 by 4O	16	12		
4 by 4O	18	12		
4 by 4O	16	16		
Hubbed				
4 by 3O	16	53/4		
4 by 4O	12	53/4		
4 by 4O	14	53/4		
4 by 4O	16	53/4		
4 by 4O	18	53/4		

^A For details of barrel, spigot, and gasket positioning lug, see Figs. 1 and 2.

FIG. 56 Closet Bend (corresponds to Table 89 of CISPI Specification 301)




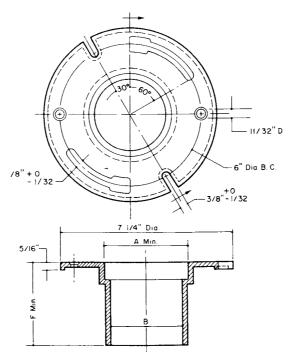

ASA Code Group 022		Cizo in	Dimensions, in. (mm)			
Item No.	V	- Size, in.	A, Minimum	В	F, Minimum	
2966	4	4 by 3 by 3½	4 (102)	3 (76)	31/2 (89)	
		4 by 3 by 8				
		4 by 3 by 10				
2970	6	4 by 4 by 4	4 (102)	4 (102)	4 (102)	
		4 by 4 by 8				

FIG. 57 Closet Flange Riser (corresponds to Table 90 of CISPI Specification 301)

DETAILS OF TAPPING BOSSES

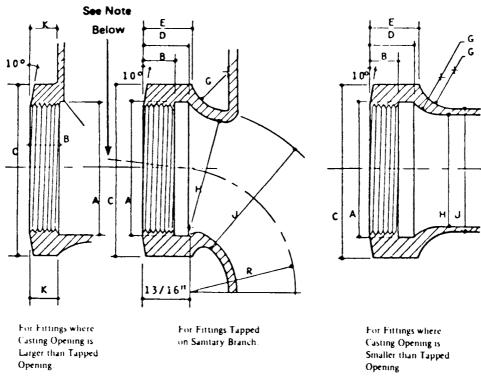


Note 1—Horizontal inlet waste bosses to be tapped at an angle of 1/4 in. (6 mm) per foot to provide flow.

Cina in	Dimensions, in. ^A									
Size, in.	Α	В	С	D	E	G	Н	J	K	R
11/4	1 15/16	7/16	211/16	3/4	7/8	1/2	11/2	1 ¹³ / ₁₆	1/2	13/4
11/2	115/16	7/16	211/16	3/4	7/8	1/2	11/2	1 13/16	1/2	13/4
2	27/16	7/16	31/4	3/4	15/16	5/8	2	25/16	1/2	21/4
21/2	3	5/8	315/16	1	1 1/8	3/4	21/2	213/16	5/8	23/4
3	39/16	3/4	45/8	13/16	1 5/16	1	3	35/16	3/4	3
31/2	41/16	3/4	51/8	11/4	13/8	1	31/2	313/16	3/4	3
4	49/16	13/16	53/4	11/4	1 7/ ₁₆	11/8	4	41/2	1 3/16	31/2
5	55/8	15/16	71/16						13/8	
6	611/16	1	85/16						17/16	
8	87/8	1	101/4						1 13/16	
10	11	11/4	12						1 ¹⁵ / ₁₆	

^A 1 in. = 25.4 mm.

FIG. 58 Dimensions for Tapping Bosses (corresponds to Table 91 of CISPI Specification 301)

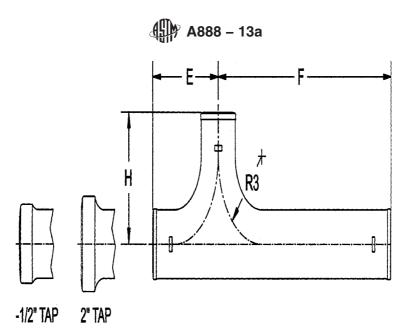


ASA Code	e Group 022	Cino in		Dimensions, in.	ons, in. ^A	
Item No.	V	—— Size, in. —	E ^B	Н	R	F ^B
0842		2 by 12	4½ (114)	4½ (114)	3 (76)	12 (305)
0843		2 by 14	41/2 (114)	4½ (114)	3 (76)	14 (356)
0844		2 by 16	41/2 (114)	4½ (114)	3 (76)	16 (406)
0846		2 by 18	41/2 (114)	4½ (114)	3 (76)	18 (457)
0848		2 by 24	4½ (114)	4½ (114)	3 (76)	24 (610)

^A For details of barrel, spigot and gasket positioning lug see Figs. 1 and 2. ^B Dimensions E and F are laying lengths.

FIG. 59 Double Sweep Sanitary Tee (Extended)



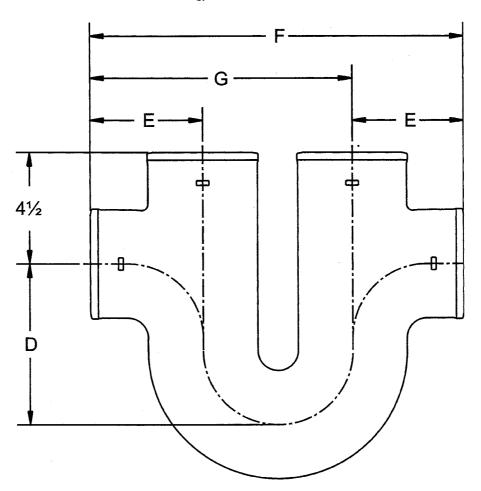



ASA Code Group 022		Cizo in		Dimensions,	in. ^A	
Item No.	V	—— Size, in. ——	D	E	F ^B	G
2524		4	6½ (165)	4½ (114)	15 (381)	10½ (267)


^A For details of barrel and spigot see Figs. 1 and 2. ^B Dimension F is laying length.

FIG. 60 Running Trap With Double Vents










Note 1-Inclusion of spigot bead and positioning lug optional with manufacturer based on casting methods used.

ASA Code	Group 022	Size, in	Dimensions, in. ^A				
Item No.	\checkmark	Size, III.	G	Н	F ^B	IPS	
2548		2	21/4 (57)	53/16 (132)	7½ (191)	1½ (38)	
2550		2	21/4 (57)	53/16 (132)	18 (457)	1½ (38)	
2552		2	3 (76)	53/16 (132)	18 (457)	11/2	

^A For details of barrel and spigot see Figs. 1 and 2. ^B Dimension F is laying length.

FIG. 61 $\,$ P Trap With $1\frac{1}{2}$ or 2 in. Tapped or Hubless Side Inlet Right or Left and Extended



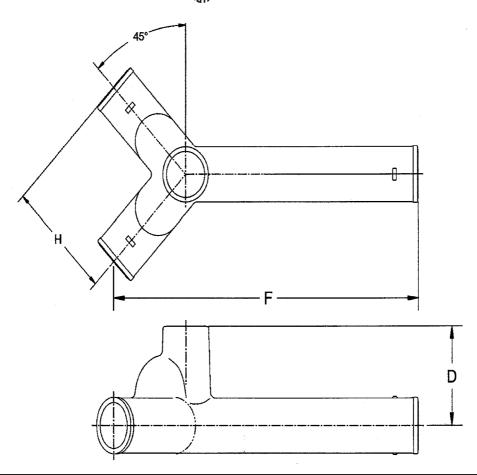


ASA C	Code Group 022	Size, in.		Dimensions, in. ^A	
Item No.	$\sqrt{}$	Size, III.	D	Н	F ^B
1374		2	41/4 (108)	51/4 (133)	15¾ (400)

^A For details of barrel and spigot see Figs. 1 and 2. ^B Dimension F is laying length.

FIG. 62 Vented Tub Wye Extended (Double)



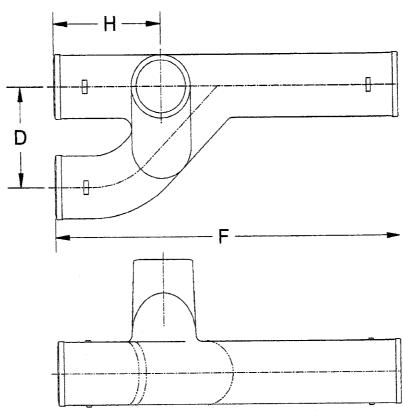


ASA Cod	de Group 022	Size, in		Dimensions, in. ^A	
Item No.	V	Size, III.	D	Н	F ^B
1376		2	3¾ (95)	41/4 (108)	13¾ (349)
1377		2	33/4 (95)	41/4 (108)	16 (406)

^A For details of barrel and spigot see Figs. 1 and 2. ^B Dimension F is laying length.

FIG. 63 Vented Tub Wye Extended Offset (Left or Right)




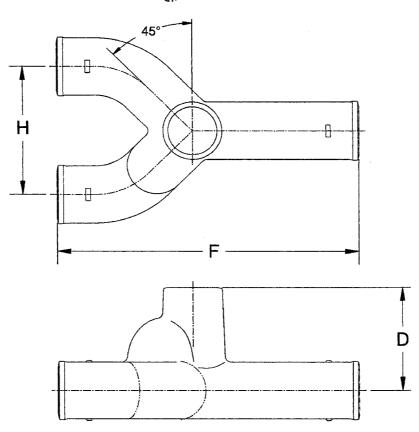

ASA Cod	e Group 022	Size, in		Dimensions, in. ^A	
Item No.	\checkmark	Size, III.	D	Н	F ^B
1378		2	41/4 (108)	51/4 (133)	15 (305)
1380		2	41/4 (108)	51/4 (133)	29½ (749)

^A For details of barrel and spigot see Figs. 1 and 2. ^B Dimension F is laying length.

FIG. 64 Vented Tub Wye

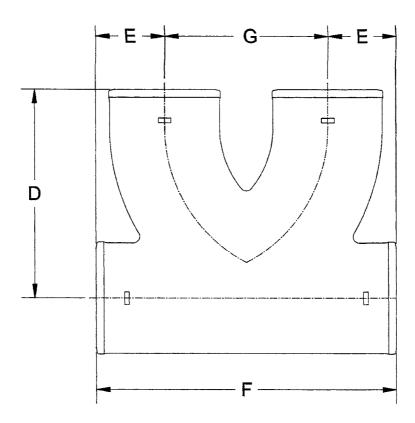

ASA Code	ASA Code Group 022			Dimension	Dimensions, in. ^A	
Item No.	V	Size, in. —	D	E	F ^B	G
		3	71/4	21/4	10	51/4
8452		4	81/4 (210)	23/4 (64)	12 (305)	6½ (165)

^A For details of barrel and spigot see Figs. 1 and 2.

FIG. 65 Double Two Way Cleanout

SUPPLEMENTARY REQUIREMENTS

The following supplementary requirements shall be applied only when specified by the purchaser. Details of the supplementary requirements shall be agreed upon by the manufacturer and the purchaser. The specified tests shall be performed by the manufacturer prior to shipment of the castings.

S1. Leak Tests on Pipe

- S1.1 Sample lengths of pipe shall be checked for leaks by subjecting them to an internal hydrostatic pressure of 20 psi (138 kPa).
- S1.2 Samples shall be taken at substantially regular intervals in the course of production so as to be representative of the material delivered and shall consist of at least 20 % of the

lengths ordered in each size. For every sample that leaks, four or more additional samples shall be taken. Each additional sample shall be representative of the same material as that of the defective sample.

S1.3 Pipes that leak shall be rejected.

 $^{^{\}it B}$ Dimension F is laying length.



ANNEX

(Mandatory Information)

A1. THIRD PARTY CERTIFICATION OR INSPECTION

INTRODUCTION

The following supplementary requirements shall be applied when the manufacturer or seller of the products covered by this specification utilizes third party certification agencies as part of their certifications as detailed in Section 13 of this specification.

- A1.1 Third Party certifiers or inspectors conducting regular inspections at the manufacturer's production facility shall include, but not be limited to, the following during each inspection.
- A1.1.1 A review of the manufacturer's records to verify compliance with 4.3, 5.1, 6.1, 12.2, and 12.3 of this specification. Copies of the manufacturer's test reports shall be added to the third party certifiers inspection report.
- A1.1.2 Random inspections of the manufacturer's finished goods inventory shall be conducted during each inspection. These inspections shall include a dimensional and marking inspection of not less than ten of these pieces of different size pipe produced during each inspection. Each pipe shall be

measured with suitable instruments or gauges and all dimensions in Fig. 1 and Fig. 2 of this specification shall be measured and recorded. This inspection report shall be furnished as part of the certification report in 13.1. Inspection of the manufacturer's finished goods inventory of fittings shall be made. Fittings shall be selected randomly and include a minimum of ten fittings during each inspection. These fittings selected shall be of different patterns or sizes or both. These fittings shall be measured with suitable gauges or instruments and all dimensions in Fig. 1, Fig. 2 and the appropriate laying length dimensions found in Figs. 5-65 shall be recorded. This inspection report shall be furnished as a part of the certification report in 13.1.

APPENDIXES

(Nonmandatory Information)

X1. ELECTRONIC DATA PROCESSING (EDP) NUMBERS

X1.1 Please take note that electronic data processing (EDP) numbers have been added. The EDP numbers indicated represent a new Uniform Industry Code adopted by the Cast Iron Soil Pipe Institute (CISPI) and the American Supply Association (ASA). A group designation prefix (022) is assigned to

hubless products, followed by the four digit identification assigned to individual items and a check digit. This system has been instituted to facilitate EDP control through distribution channels, and should now be used universally in ordering and specifying product items.

X2. PROCEDURES FOR SOIL SURVEY TESTS AND OBSERVATIONS AND THEIR INTERPRETATION TO DETERMINE WHETHER CAST IRON PIPE FOR WASTE WATER OR OTHER LIQUIDS REQUIRES POLYETHYLENE ENCASEMENT

X2.1 Scope

X2.1.1 In the appraisal of soil and other conditions that affect the corrosion rate of cast iron pipe, a minimum number of factors must be considered. They are outlined in the following sections. A method of evaluating and interpreting each factor and a method of weighting each factor to determine whether polyethylene encasement should be used are subsequently described.

X2.2 Earth Resistivity

X2.2.1 There are three methods for determining earth resistivity: four-pin, single-probe, and soil-box. In the field, a

four-pin determination should be made with pins spaced at approximate pipe depth. This method yields an average of resistivity from the surface to a depth equal to pin spacing. However, results are sometimes difficult to interpret where dry top soil is underlaid with wetter soils and where soil types vary with depth. The Wenner configuration is used in conjunction with a resistivity meter. For all-around use, a unit with a capacity of up to 10^4 ohms is suggested because of its versatility in permitting both field and laboratory testing in most soils.

X2.2.2 Because of the aforementioned difficulty in interpretation, the same unit may be used with a single probe

that yields resistivity at the point of the probe. A boring is made into the subsoil so that the probe may be pushed into the soil at the desired depth.

X2.2.3 Inasmuch as the soil may not be typically wet, a sample should be removed for resistivity determination, which may be accomplished with any one of several laboratory units that permits the introduction of water to saturation, thus stimulating saturated field conditions. Each of these units is used in conjunction with a soil resistivity meter.

X2.2.4 Interpretation of resistivity results is extremely important. To base an opinion on a four-pin reading with dry top soil averaged with wetter subsoil would probably result in an inaccurate premise. Only by reading the resistivity in soil at pipe depth can an accurate interpretation be made. Also, every effort should be made to determine the local situation concerning ground-water table, presence of shallow ground water, and approximate percentage of time the soil is likely to be water-saturated.

X2.2.5 With cast iron pipe, corrosion protection provided by products of corrosion is enhanced if there are dry periods during each year. Such periods seem to permit hardening or toughening of the corrosion scale or products, which then become impervious and serve as better insulators.

X2.2.6 In making field determinations of resistivity, temperature is important. The result obtained increases as temperature decreases. As the water in the soil approaches freezing, resistivity increases greatly, and, therefore, is not reliable. Field determinations under frozen soil conditions should be avoided. Reliable results under such conditions can be obtained only by collection of suitable subsoil samples for analysis under laboratory conditions at suitable temperature.

X2.2.7 Interpretation of Resistivity —Because of the wide variance in results obtained under the methods described, it is difficult specifically to interpret any single reading without knowing which method was used. It is proposed that interpretation be based on the lowest reading obtained with consideration being given to other conditions, such as normal moisture content of the soil in question. Because of the lack of exact correlation between experiences and resistivity, it is necessary to assign ranges of resistivity rather specific numbers. In Table X2.1, points are assigned to various ranges of resistivity. These points, when considered along with points assigned to other soil characteristics, are meaningful.

X2.3 pH

X2.3.1 In the pH range from 0.0 to 4.0, the soil serves well as an electrolyte, and total acidity is important. In the pH range from 6.5 to 7.5, soil conditions are optimum for sulfate reduction. In the pH range from 8.5 to 14.0, soils are generally quite high in dissolved salts, yielding a low soil resistivity.

X2.3.2 In testing pH, glass and reference electrodes are pushed into the soil sample and a direct reading is made following suitable temperature setting on the instrument. Normal procedures are followed for standardization.

TABLE X2.1 Soil-Test Evaluation^A

Soil Characteristics	Points
Resistivity, ohm-cm (based on single probe at pipe	depth or water-saturated
soil-box):	
<1500	10
≧1500 to 1800	8
≥1800 to 2100	5
≥2100 to 2500	2
≥2500 to 3000	1
>3000	0
pH:	
0–2	5
2–4	3
4–6.5	0
6.5–7.5	0 ^B
7.5–8.5	0
>8.5	3
Redox potential:	
> +100 mV	0
+50 to +100 mV	3.5
0 to +50 mV	4
Negative	5
Sulfides:	
Positive	3.5
Trace	2
Negative	0
Moisture:	
Poor drainage, continuously wet	2
Fair drainage, generally moist	1
Good drainage, generally dry	0

^A Ten points = corrosive to cast iron pipe; protection indicated.

X2.4 Oxidation-Reduction (Redox) Potential

X2.4.1 The oxidation-reduction (redox) potential of a soil is significant because the most common sulfate-reducing bacteria can live only under anaerobic conditions. A redox potential greater than +100 mV shows the soil to be sufficiently aerated so that it will not support sulfate reducers. Potentials of 0 to +100 mV may or may not indicate anaerobic conditions under which sulfate reducers thrive. This test also is accomplished using a portable pH meter, with platinum and reference electrodes inserted into the soil sample, which permits a reading of potential between the two electrodes. It should be noted that soil samples removed from a boring or excavation can undergo a change in redox potential on exposure to air. Such samples should be tested immediately on removal from the excavation. Experience has shown that heavy clays, muck, and organic soils are often anaerobic, and these soils should be regarded as potentially corrosive.

X2.5 Sulfides

X2.5.1 The sulfide determination is recommended because of its field expediency. A positive sulfide reaction reveals a potential problem due to sulfate-reducing bacteria. The sodium azide-iodine qualitative test is used. In this determination, a solution of 3 % sodium azide in a 0.1 N iodine solution is introduced into a test tube containing a sample of the soil in question. Sulfides catalyze the reaction between sodium azide and iodine, with the resulting evolution of nitrogen. If strong bubbling or foaming results, sulfides are present, and the presence of sulfate-reducing bacteria is indicated. If very slight

^B If sulfides are present and low or negative redox potential results are obtained, three points shall be given for this range.

bubbling is noted, sulfides are probably present in small concentration, and the result is noted as a trace.

X2.6 Moisture Content

X2.6.1 Since prevailing moisture content is extremely important to all soil corrosion, every effort must be made to determine this condition. It is not proposed, however, to determine specific moisture content of a soil sample, because of the probability that content varies throughout the year, but to question local authorities who are able to observe the conditions many times during the year. (Although mentioned in X2.2, this variability factor is being reiterated to emphasize the importance of notation.)

X2.7 Soil Description

X2.7.1 In each investigation, soil types should be described completely. The description should include color and physical characteristics, such as particle size, plasticity, friability, and uniformity. Observation and testing will reveal whether the soil is high in organic content; this should be noted. Experience has shown that in a given area, corrosivity may often be reflected in certain types and colors of soil. This information is valuable for future investigations or for determining the most likely soils to suspect. Soil uniformity is important because of the possible development of local corrosion cells due to the difference in potential between unlike soil types, both of which are in contact with the pipe. The same is true for uniformity of aeration. If one segment of soil contains more oxygen than a neighboring segment, a corrosion cell can develop from the difference in potential. This cell is known as a differential aeration cell.

X2.7.2 There are several basic types of soil that should be noted: sand, loam, silt, clay, and muck. Unusual soils, such as peat, or soils high in foreign material, should also be noted and described.

X2.8 Potential Stray Direct Current

X2.8.1 Any soil survey should include consideration of possible stray direct current with which the cast iron pipe

installation might interfere. The widespread use of rectifiers and ground beds for cathodic protection of underground structures has resulted in a considerable threat from this source. Proximity of such cathodic protection systems should be noted. Among other potential sources of stray direct current are electric railways, industrial equipment, including welding, and mine transportation equipment.

X2.9 Experience With Existing Installations

X2.9.1 The best information on corrosivity of soil with respect to cast iron pipe is the result of experience with these materials in the area in question. Every effort should be made to acquire such data by questioning local officials and, if possible, by actual observation of existing installations.

X2.10 Soil-Test Evaluation

X2.10.1 Using the soil-test procedures described in this specification, the following tests are considered in evaluating corrosivity of the soil: resistivity, pH, redox potential, sulfides, and moisture. For each of these tests, results are categorized according to their contribution to corrosivity. Points are assigned based on experience with gray and ductile cast iron pipe. When results of these five test observations are available, the assigned points are totaled. If the sum is equal to ten or more, the soil is corrosive to cast iron pipe and protection against exterior corrosion should be provided. This system is limited to soil corrosion and does not include consideration of stray direct current. Table X2.1 lists points assigned to the various test results.

X2.11 General

X2.11.1 These notes deal only with cast iron pipe, the soil environment in which they will serve, and methods of determining the need for polyethylene encasement. When it is determined that a soil environment is corrosive to cast iron, the practice outlined in Appendix X3 should be used.

X3. POLYETHYLENE ENCASEMENT FOR CAST IRON PIPE FOR WASTE WATER

X3.1 Scope

X3.1.1 This practice covers materials and installation procedures for polyethylene encasement to be applied to underground installations of cast iron pipe. It is also used for polyethylene encasement of fittings, and other appurtenances to cast iron pipe systems.

X3.1.2 This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.

X3.2 Referenced Documents

X3.2.1 *ASTM Standard*: ³D1248 Specification for Polyethylene Plastics Extrusion Materials for Wire and Cable

X3.3 Terminology

X3.3.1 Definitions:

X3.3.1.1 *polyethylene encasement, n*—polyethylene material, in tube or sheet form, that is used to encase cast iron pipe.

X3.3.1.2 *securing overlap, n*—any one of various methods of holding polyethylene encasement in place at the point of overlap until backfilling operations are completed. This may be accomplished with adhesive tape, plastic string, or other suitable material.

X3.4 Requirements

X3.4.1 Materials:

- X3.4.1.1 Low-Density Polyethylene Film—Low-density polyethylene film shall be manufactured of virgin polyethylene material conforming to the requirements of Table 2 in Specification D1248.
- (1) Thickness—Low-density polyethylene film shall have a minimum nominal thickness of 0.008 in. (0.20 mm). The minus tolerance on thickness shall not exceed 10 % of the nominal thickness.
- X3.4.1.2 High-Density Cross-Laminated Polyethylene Film—High-density cross-laminated polyethylene film shall be manufactured of virgin polyethylene material conforming to the requirements of Specification D1248 as shown in Table X3.1.
- (1) Thickness—High-density cross-laminated polyethylene film shall have a minimum nominal thickness of 0.004 in. (0.10 mm). The minus tolerance on thickness shall not exceed $10\,\%$ of the nominal thickness.
- X3.4.2 *Tube Size*—The tube size for each pipe diameter shall be as listed in Table X3.2.

X3.5 Installation

Dielectric strength

X3.5.1 General:

X3.5.1.1 The polyethylene encasement shall prevent contact between the pipe and the surrounding backfill and bedding material but is not intended to be a completely airtight or watertight enclosure. All lumps of clay, mud, cinders, and the like, that are on the pipe surface shall be removed prior to installation of the polyethylene encasement. During installation, care shall be exercised to prevent soil or embedment material from becoming entrapped between the pipe and the polyethylene.

X3.5.1.2 The polyethylene film shall be fitted to the contour of the pipe to affect a snug, but not tight, encasement with minimum space between the polyethylene and the pipe. Sufficient slack shall be provided in contouring to prevent stretching the polyethylene, bridging irregular surfaces, such as hubspigot interfaces, coupled joints, or fittings, and to prevent damage to the polyethylene due to backfilling operations. Overlaps and ends shall be secured by the use of adhesive tape, string, plastic tie straps, or any other material capable of holding the polyethylene encasement in place until backfilling operations are completed.

X3.5.1.3 For installations below the water table or in areas subject to tidal actions, or both, it is recommended that tube-form polyethylene be used with both ends sealed as thoroughly as possible with adhesive tape or plastic tie straps

TABLE X3.1 Polyethylene Characteristics

Raw Material Used to Manufacture Polyethylene Encasement Material					
Type, class, grade, other characteristics in accordance with the latest revision of Specification D1248:					
Туре	1				
Class	A—Natural color or C—Black				
Grade	E1				
Flow rate, g/10 min	0.4 max				
Dielectric strength, volume resistivity	10 ¹⁵ ⋅cm ³ , min				
Polyethylene Er	ncasement Material				
Tensile strength	1200 psi (8 MPa), min				
Elongation	300 %, min				

TABLE X3.2 Polyethylene Tube Sizes

Nominal Pipe Diameter, in.	Recommended Polyethylene Flat Tube Width, in. (cm) ^A
1½ , 2, 3	14 (35)
4	16 (41)
6	20 (51)
8	24 (61)
10	27 (69)
12	30 (76)
14	34 (86)
15	37 (94)

^A For flat sheet polyethylene, see X3.5.2.3.

at the joint overlap. It is also recommended that circumferential wraps of tape or plastic tie straps be placed at 2-ft (0.6-m) intervals along the barrel of the pipe to help minimize the space between the polyethylene and the pipe.

X3.5.2 *Pipe*—This practice includes three different methods for the installation of polyethylene encasement. Method A and B are for use with polyethylene tubes, and Method C is for use with polyethylene sheets.

X3.5.2.1 *Method A* (see Fig. X3.1):

- (1) Cut the polyethylene tube to a length approximately 2 ft (0.6 m) longer than the length of the pipe section. Slip the tube around the pipe, centering it to provide a 1-ft (0.3-m) overlap on each adjacent pipe section, and bunching it accordion fashion lengthwise until it clears the pipe ends.
- (2) Lower the pipe into the trench and make up the pipe joint with the preceding section of pipe. A shallow bell hole must be made at joints to facilitate installation of the polyethylene tube.
- (3) After assembling the pipe joint, make the overlap of the polyethylene tube. Pull the bunched polyethylene from the preceding length of pipe, slip it over the end of the new length of pipe, and secure in place. Then slip the end of the polyethylene from the new pipe section over the end of the first wrap until it overlaps the joint at the end of the preceding length of pipe. Secure the overlap in place. Take up the slack width at the top of the pipe as shown in Fig. X3.2, to make a snug, but not tight, fit along the barrel of the pipe, securing the fold at quarter points.
- (4) Repair any rips, punctures, or other damage to the polyethylene with adhesive tape or with a short length of polyethylene tube cut open, wrapped around the pipe, and secured in place. Proceed with installations of the next section of pipe in the same manner.
- X3.5.2.2 Cut the polyethylene tube to a length approximately 1 ft (0.3 m) shorter than the length of the pipe section. Slip the tube around the pipe, centering it to provide 6 in. (150 mm) of bare pipe at each end. Make the polyethylene snug, but not tight, as shown in Fig. X3.2; secure ends as described in X3.5.2.1
- X3.5.2.3 Before making up a joint, slip a 3-ft (0.9-m) length of polyethylene tube over the end of the preceding pipe section, bunching it accordion fashion lengthwise. After completing the joint, pull the 3-ft length of polyethylene previously installed on each adjacent section of pipe by at least 1 ft (0.3 m); make snug and secure each end as described in X3.5.2.1.

800 V/mil (31.5 V/um) thickness, min




FIG. X3.1 Method A Hubless Pipe

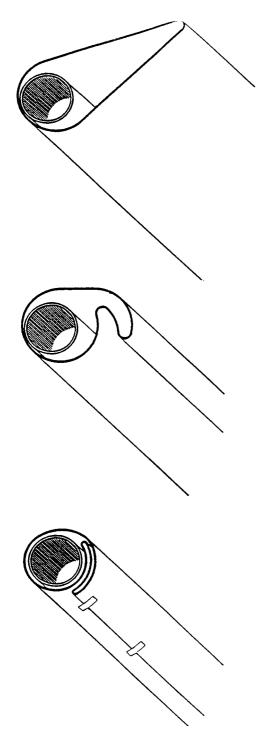


FIG. X3.2 Method A Slack Reduction Procedure

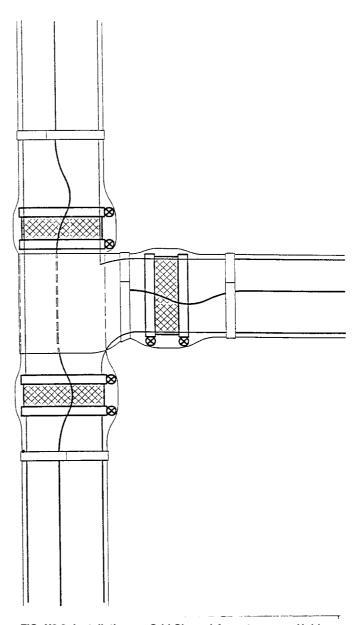


FIG. X3.3 Installation on Odd-Shaped Appurtenances Hubless Pipe

X3.5.2.4 Repair any rips, punctures, or other damage to the polyethylene as described in X3.5.2.1. Proceed with installation of the next section of pipe in the same manner.

X3.5.3 Flat sheet polyethylene shall have a minimum width twice the flat tube width shown in Table X3.3.

X3.5.3.1 Cut the polyethylene sheet to a length approximately 2 ft (0.6 m) longer than the length of pipe section. Center the cut length to provide a 1-ft (0.3-m) overlap on each adjacent pipe section, bunching it until it clears the pipe ends. Wrap the polyethylene around the pipe so that it overlaps circumferentially over the top quadrant of the pipe. Secure the cut edge of polyethylene sheet at approximately 3-ft (0.9-m) intervals along the pipe length.

X3.5.3.2 Lower the wrapped pipe into the trench and make up the pipe joint with the preceding section of pipe. A shallow hub hole must be made at joints to facilitate installation of the polyethylene. After completing the joint, make the overlap as described in X3.5.2.1.

TABLE X3.3 High-Density Cross-Laminated Polyethylene Characteristics

Raw Material Used to Manufacture Polyethylene Encasement Material

Type, class, grade, other characteristics in accordance with the latest revision of Specification D1248:

Type 11

Class A—Natural color, B—Colors, or

C—Black P33

Grade P33
Flow rate, g/10 min 0.4 to 0.5 g/10 min

Dielectric strength, volume resistivity

0.4 to 0.5 g/10 min

High-Density Cross-Laminated Polyethylene Encasement Material

Tensile strength 5000 psi (34.6 MPa), min

Elongation 100 %, min

Dielectric strength 800 V/mil (31.5 V/µm) thickness, min

X3.5.3.3 Repair any rips, punctures, or other damage to the polyethylene as described in X3.5.2.1. Proceed with installation of the next section of pipe in the same manner.

X3.5.4 *Pipe-Shaped Appurtenances* —Bends, reducers, offsets, and other pipe-shaped appurtenances shall be covered with polyethylene in the same manner as the pipe.

X3.5.5 Odd-Shaped Appurtenances—Wrap tees, crosses, and other odd-shaped pieces that cannot practically be wrapped in a tube with a flat sheet or split length of polyethylene tube. Pass the sheet under the appurtenance and bring up around the body. Make seams by bringing the edges together, folding over twice, and taping down (see Fig. X3.3). Handle slack width and overlaps at joints as described in X3.5.2.1. Tape polyethylene securely in place.

X3.5.6 *Repairs*—Repair any cuts, tears, punctures, or damage to polyethylene with adhesive tape or with a short length of polyethylene tube cut open, wrapped around the pipe covering the damaged area, and secured in place.

X3.5.7 Junctions Between Wrapped and Unwrapped Pipe—Where polyethylene-wrapped pipe joins a pipe that is not wrapped, extend the polyethylene tube to cover the unwrapped pipe a distance of at least 3 ft (0.9 m). Secure the end with circumferential turns of tape.

X3.5.8 Backfill for Polyethylene-Wrapped Pipe—Backfill material shall be the same as specified for pipe without polyethylene wrapping. Take special care to prevent damage to the polyethylene wrapping when placing backfill. Backfill material shall be free of cinders, refuse, boulders, rocks, stones, or other material that could damage polyethylene.

ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.

This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.

This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org). Permission rights to photocopy the standard may also be secured from the ASTM website (www.astm.org/COPYRIGHT/).